



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

## Composition–solubility–structure relationships in calcium (alkali) aluminosilicate hydrate (C-(N,K-)A-S-H)

### Citation for published version:

Myers, RJ, L'Hopital, E, Provis, JL & Lothenbach, B 2015, 'Composition–solubility–structure relationships in calcium (alkali) aluminosilicate hydrate (C-(N,K-)A-S-H)' Dalton Transactions, vol 44, pp. 13530-13544. DOI: 10.1039/C5DT01124H

### Digital Object Identifier (DOI):

[10.1039/C5DT01124H](https://doi.org/10.1039/C5DT01124H)

### Link:

[Link to publication record in Edinburgh Research Explorer](#)

### Document Version:

Peer reviewed version

### Published In:

Dalton Transactions

### General rights

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

### Take down policy

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact [openaccess@ed.ac.uk](mailto:openaccess@ed.ac.uk) providing details, and we will remove access to the work immediately and investigate your claim.



# Composition-solubility-structure relationships in calcium (alkali) aluminosilicate hydrate (C-(N,K-)A-S-H)

Rupert J. Myers<sup>1,2,a</sup>, Emilie L'Hôpital<sup>2,b</sup>, John L. Provis<sup>1,c</sup>, Barbara Lothenbach<sup>2\*</sup>

<sup>1</sup> Department of Materials Science and Engineering, University of Sheffield, S1 3JD,  
Sheffield, United Kingdom

<sup>2</sup> Laboratory for Concrete and Construction Chemistry, EMPA, Dübendorf, 8600, Switzerland

\* Corresponding author. Email [Barbara.Lothenbach@empa.ch](mailto:Barbara.Lothenbach@empa.ch)

<sup>a</sup> [rupert.myers@gmail.com](mailto:rupert.myers@gmail.com). <sup>b</sup> [lhospital.emilie@gmail.com](mailto:lhospital.emilie@gmail.com). <sup>c</sup> [j.provis@sheffield.ac.uk](mailto:j.provis@sheffield.ac.uk).

## Abstract

The interplay between the solubility, structure and chemical composition of calcium (alkali) aluminosilicate hydrate (C-(N,K-)A-S-H) equilibrated at 50°C is investigated in this paper. The tobermorite-like C-(N,K-)A-S-H products are more crystalline in the presence of alkalis and generally have larger basal spacings at lower Ca/Si ratios. Both Na and K are incorporated into the interlayer space of the C-(N,K-)A-S-H phases, with more alkali uptake observed at higher alkali and lower Ca content. No relationship between Al and alkali uptake is identified at the Al concentrations investigated ( $\text{Al/Si} \leq 0.1$ ). More stable C-(N,K-)A-S-H is formed at higher alkali content, but this factor is only significant in some samples with  $\text{Ca/Si} \leq 1$ . Shorter chain lengths are formed at higher alkali and Ca content, and cross-

linking between (alumino)silicate chains in the tobermorite-like structure is greatly promoted by increasing alkali and Al concentrations. The calculated solubility products do not depend greatly on the mean chain length in C-(N,K-)A-S-H at a constant Ca/(Al+Si) ratio, or the Al/Si ratio in C-(N,K-)A-S-H. These results are important for understanding the chemical stability of C-(N,K-)A-S-H, which is a key phase formed in the majority of cements and concretes used worldwide.

## 1. Introduction

The alkali concentration in cement-based materials varies greatly as a function of the cement formulation and type: Portland cement (PC) typically contains up to 1 wt.% alkali (mainly K) oxide equivalent;<sup>1</sup> fly ash, a common supplementary cementitious material (SCM), generally contains >1 wt.% alkali (Na + K) oxide equivalent;<sup>2</sup> and alkali-activated cementitious materials typically involve the use of highly concentrated Na-based solutions (up to or exceeding 5 M).<sup>3</sup> The elevated pH environment that prevails in hydrated cement-based materials (pH > 13) provides the crucial function of steel passivation in reinforced concrete. The alkali concentration in cement-based materials also plays an important role in the dissolution of cementitious precursors,<sup>4, 5</sup> deterioration of concrete due to alkali-silica reactions,<sup>6, 7</sup> and in modifying the chemical composition, structure and solubility of reaction products formed during setting and hardening.<sup>8-11</sup>

The main reaction product in hydrated Portland cement (PC) materials is calcium (alkali) silicate hydrate (C-(N,K-)S-H<sup>a</sup>) with a structure analogous to the natural mineral

---

<sup>a</sup> Na and K are included in this abbreviation because these are typically the most concentrated alkali elements in cement-based materials. Cement chemistry notation is also used throughout the paper: C = CaO; S = SiO<sub>2</sub>; A = Al<sub>2</sub>O<sub>3</sub>; N = Na<sub>2</sub>O; K = K<sub>2</sub>O; and H = H<sub>2</sub>O.

tobermorite, usually with  $\text{Ca}/(\text{Al}+\text{Si}) \geq 1.5$ , and sometimes with minor Al substitution up to an Al/Si ratio not exceeding 0.1.<sup>12</sup> This phase contains silicate (or aluminosilicate if Al is present) chains in dreierketten type arrangements, flanked on either side by a Ca-O sheet and an interlayer region (Figure 1).<sup>13</sup> These aluminosilicate chains can cross-link to form  $\text{Q}^3$ -type structures,<sup>14</sup> and if present, Al is bound in bridging sites with a strong preference over the paired sites.<sup>15</sup> Al is also thought to be incorporated in C-(N,K-)A-S-H in five- and six-fold coordination, *e.g.* in the interlayer (Figure 1), although no consensus exists regarding the location of octahedral Al in this phase.<sup>16-18</sup> The Ca-O sheets, interlayer regions and (alumino)silicate chains are thought to stack together such that the chain structures form the external surfaces.<sup>19</sup>

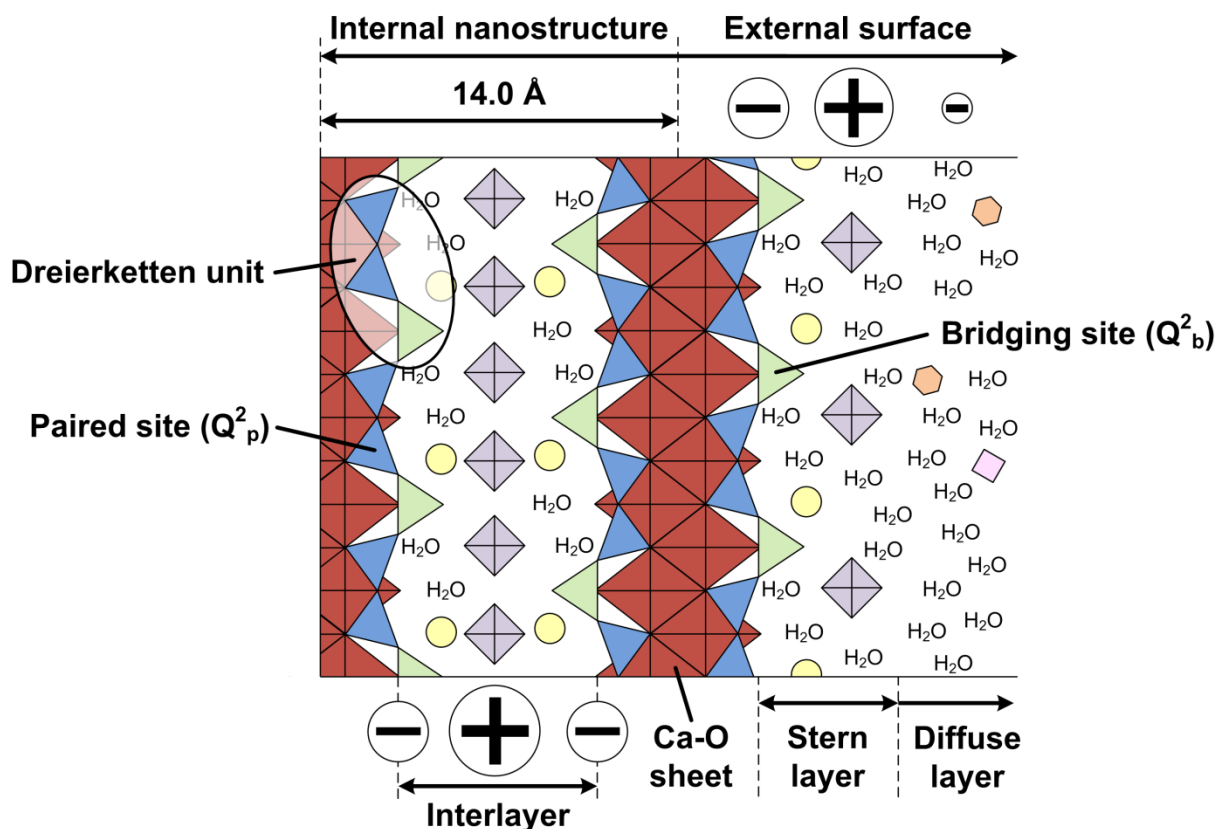


Figure 1. Schematic representation of infinite chain length non-cross-linked C-(N,K-)A-S-H as a structural analogue of 14 Å tobermorite,<sup>20</sup> with stacked layers to show alkali species adsorbed on the external surface and in the interlayer region of this phase. The red diamonds are CaO polyhedra in the Ca-O sheet, and the blue and green triangles are tetrahedral aluminate or silicate units in paired and bridging sites respectively, within the dreierketten chains. The yellow circles and large purple squares represent positively-charged species that charge-neutralise the bridging sites and the rest of the layered structure respectively (typically  $\text{H}^+$ ,  $\text{Ca}^{2+}$ , alkali cations such as  $\text{K}^+$  or  $\text{Na}^+$ , and/or dissolved aluminium). The orange hexagons are diffuse layer anions (*e.g.*  $\text{OH}^-$  and  $\text{Cl}^-$ ) that compensate the excess positive charge supplied by adsorbed cations.<sup>19</sup> The small pink square is an additional diffuse layer cation (*e.g.*  $\text{Ca}^{2+}$ ,  $\text{Na}^+$ ). The positive and negative symbols represent the local distribution of charge in the structure. The size, number and location of the symbols are schematic rather than crystallographically exact, and different types of hydrated alkali complexes are not distinguished.

The essentially aluminium-free C-(N,K-)S-H formed during plain Portland cement hydration can incorporate a significant content of alkalis (up to 20% of the amount of Na or K added<sup>21</sup>), which decreases as a direct function of the Ca/Si ratio.<sup>21</sup> A good understanding of C-(N,K-)S-H solubility currently exists up to bulk Na concentrations of 0.8 M NaOH,<sup>8, 9, 21-24</sup> which represents the pH range relevant to most cement-based materials ( $\text{pH} \leq 13.5$ ), but fewer solubility data for this phase are available for K-containing materials in the

corresponding composition range.<sup>21, 22, 25, 26</sup> These data are essential in understanding the long-term stability of C-(N,K-)S-H and in the development of thermodynamic models for this phase, enabling simulation of the chemistry of cement-based materials in service.<sup>27, 28</sup>

However, many modern blended cements contain more Al and less Ca than plain PC. The main hydrate in binders produced from these materials is a calcium (alkali) aluminosilicate hydrate (C-(N,K-)A-S-H<sup>b</sup>) with typical molar ratios of  $\text{Ca}/(\text{Al}+\text{Si}) \leq 1.5$  and  $\text{Al}/\text{Si} > 0.1$ .<sup>29, 30</sup> C-(N,K-)A-S-H phases are also major reaction products in ~2000 year old Roman cements.<sup>31</sup> Incorporation of alkali species into the interlayer region and on external surfaces of C-(N,K-)A-S-H is believed to occur via a charge-compensation mechanism (Figure 1),<sup>11, 19, 32, 33</sup> with less associated alkalis at higher Ca/Si ratios (similar to C-(N,K-)S-H),<sup>34</sup> although no consensus exists regarding the exact mechanism of alkali uptake in this phase. This is corroborated by the large variation in existing results reported for Na and K uptake as a function of Al content in C-(N,K-)A-S-H: direct correlations,<sup>33, 34</sup> an inverse correlation,<sup>25</sup> and independent relationships<sup>6, 11, 35</sup> between these two parameters have been reported. There is also a lack of consensus on the selectivity of C-(N,K-)A-S-H structures between Na or K species, with existing publications reporting either no significant difference between uptake of these two alkali types,<sup>8, 21, 25, 34</sup> or some degree of selectivity for K over Na.<sup>11</sup> This clearly demonstrates a need for additional studies to clarify the relationships between the uptake of Na, K and Al in C-(N,K-)A-S-H.

The solubility of Al-containing C-(N,K-)A-S-H is poorly understood relative to that of C-(N,K-)S-H, although recent results<sup>14</sup> indicate that the solubilities of these phases do not differ significantly in the absence of alkali. The availability of a comprehensive set of solubility

---

<sup>b</sup> This notation includes products with and without Al (*i.e.* C-(N,K-)S-H), although effort is made to distinguish these phases in the text.

data for C-(N,K-)A-S-H is necessary for the development of more accurate thermodynamic models for this phase,<sup>28</sup> which would advance the utility of thermodynamic modelling in the description and performance prediction of cement-based materials. Therefore, this paper aims to clarify the effects of Na, K, Al and Ca on the chemical composition, structure, and solubility of C-(N,K-)A-S-H, utilising a dataset for C-(N,K-)A-S-H equilibrated at 50°C. The results presented are particularly relevant for cements used for construction in large structures which experience a significant semi-adiabatic temperature rise during hydration (e.g. dams or foundations), or in warm climates. The results are also discussed with respect to existing solubility data at ambient conditions.

## **2. Materials and methods**

### **2.1 C-(N,K-)A-S-H synthesis**

C-(N,K-)A-S-H samples were synthesised at bulk molar Al/Si ratios ( $\text{Al/Si}^*$ ) of 0 to 0.1 and bulk molar Ca/Si ratios ( $\text{Ca/Si}^*$ ) of 0.6 to 1.6 using Milli-Q water (Merck Millipore) and 0 to 1 M solutions of NaOH and/or KOH (Merck Millipore), at a solution/solid ratio of 45 in a N<sub>2</sub>-filled glovebox by the method described in <sup>8, 14</sup>. Samples were equilibrated at 50°C in polyethylene vessels and shaken twice per week, then filtered in a N<sub>2</sub>-filled glovebox 56 days after synthesis, and freeze-dried for a week. Freeze-dried solids were stored in N<sub>2</sub>-filled desiccators at ~30% relative humidity (over saturated CaCl<sub>2</sub> solutions) until analysis.

### **2.2 Experimental characterisation techniques**

A Dionex DP ICS-3000 ion chromatograph was used to determine Ca, Si, Al, Na and K concentrations in the filtrates (relative measurement error  $\pm 10\%$  in the concentration range of

interest). Aqueous hydroxide concentrations were determined at  $\sim 24^{\circ}\text{C}$  with a Knick pH meter (pH-Meter 766) and a Knick SE100 electrode, which was calibrated against KOH or NaOH solutions of known concentrations. Thermogravimetric analysis (TGA) was performed using a Mettler Toledo TGA/SDTA851<sup>°</sup> at a heating rate of  $20^{\circ}\text{C}/\text{min}$  under an  $\text{N}_2$  atmosphere, and derivative thermograms were calculated numerically. Powder XRD patterns were recorded on a PANalytical X'Pert Pro MDF diffractometer using a Ge(111) Johansson monochromator for Cu  $\text{K}\alpha$  radiation, an X'Celerator detector, and a step size of  $0.017^{\circ} 2\theta$ . An external  $\text{CaF}_2$  standard was used for Rietveld analysis to quantify of the amount of crystalline phases in each sample.<sup>36</sup> The ion chromatography (IC) and pH measurements, initial synthesis conditions, and solid phase assemblages and water content as determined by TGA, XRD and Rietveld analysis, were used in mass balance calculations to determine chemical compositions of the C-(N,K-)A-S-H products formed.

Solid-state  $^{29}\text{Si}$  magic angle spinning nuclear magnetic resonance (MAS NMR) spectra were collected for the Al-free and  $\text{Al}/\text{Si}^* = 0.1$  samples synthesised with water, with 0.5 M NaOH, and with 0.5 M NaOH and 0.5 M KOH (denoted 0.5 M NaOH/0.5 M KOH) at 79.49 MHz on a Bruker Avance 400 MHz NMR spectrometer with a 7 mm CP/MAS probe. The measurements were recorded using a 4500 Hz spinning rate, 9216 scans,  $\pi/3$  pulses of 2.5  $\mu\text{s}$ , and a 20 s relaxation delay.  $^{29}\text{Si}$  chemical shifts were referenced to external tetramethylsilane. Spectral deconvolutions were carried out using component peaks with a Lorentzian/Gaussian ratio of 0.5, full width at half height  $\leq 3$  ppm, and peak amplitudes constrained to be consistent with the tobermorite-like structures present in C-(N,K-)A-S-H (Appendix S1, Electronic Supporting Information).<sup>37</sup> The percentages of Al in the cross-linked components ( $\text{Al}_{[\text{C}]}$ ) of the C-(N,K-)A-S-H products formed here are calculated using the 'Cross-linked Substituted Tobermorite Model' (CSTM) (eq.(1)):<sup>37</sup>



$$Al_{[C]} = 100 \frac{(Al/Si)_{[C]} [Q^1 + Q^2(1Al) + Q^2 + Q^3(1Al) + Q^3]_{[C]}}{\sum_k ((Al/Si)_k [Q^1 + Q^2(1Al) + Q^2 + Q^3(1Al) + Q^3]_k)} \quad (1)$$

where the cross-linked and non-cross-linked components of C-(N,K-)A-S-H are represented by subscripts  $[C]$  and  $[NC]$  respectively,  $k \in \{[C], [NC]\}$  and the Al/Si fractions in this formula are calculated according to eqs.(2,3):

$$(Al/Si)_{[C]} = \frac{Q^3(1Al)}{Q^1 + Q^2 + Q^2(1Al) + Q^3 + Q^3(1Al)} \quad (2)$$

$$(Al/Si)_{[NC]} = \frac{(\frac{1}{2})Q^2(1Al)}{Q^1 + Q^2 + Q^2(1Al)} \quad (3)$$

These parameters are used directly in eq.(4) to calculate overall Al/Si ratios of the C-(N,K-)A-S-H products formed here; this correctly describes the composition of mixed cross-linked/non-cross-linked C-(N,K-)A-S-H according to the CSTM formulation:<sup>37</sup>


$$(Al/Si)_{C-(N,K-)A-S-H} = \frac{\left[ \frac{(Al/Si)_{[NC]}}{(1 + (Al/Si)_{[NC]})} (Al + Si)_{[NC]} + \frac{(Al/Si)_{[C]}}{(1 + (Al/Si)_{[C]})} (Al + Si)_{[C]} \right]}{\left[ \frac{1}{(1 + (Al/Si)_{[NC]})} (Al + Si)_{[NC]} + \frac{1}{(1 + (Al/Si)_{[C]})} (Al + Si)_{[C]} \right]} \quad (4)$$

where  $(Al + Si)$  indicates the total amount of Al and Si in a C-(N,K-)A-S-H component ( $[C]$  or  $[NC]$ ).

## 2.3 Thermodynamic modelling

Thermodynamic modelling was performed in the GEM Selektor v.3 software (<http://gems.web.psi.ch/>)<sup>38, 39</sup> using the PSI/Nagra 12/07 thermodynamic database,<sup>40</sup> which is updated from<sup>41</sup> via the inclusion of two additional aqueous (alumino)silicate species, and the CEMDATA07 thermodynamic database<sup>42-49</sup> updated to include recently published data for Al(OH)<sub>3</sub>, hydrogarnet and C-(N,K-)A-S-H.<sup>28, 50, 51</sup> Activity coefficients were calculated using the extended Debye-Hückel equation (in Truesdell-Jones form) with the ion size and extended term parameter for KOH ( $\bar{a} = 3.67 \text{ \AA}$  and  $b_\gamma = 0.123 \text{ kg/mol}$ ).<sup>52</sup> The thermodynamic properties of the aqueous species and solid phases used in these calculations are shown in Appendix S2 (Electronic Supporting Information).

Solubility products ( $K_s$ ) for C-(N,K-)A-S-H were calculated from the generalised dissolution reaction shown in eq.(5):

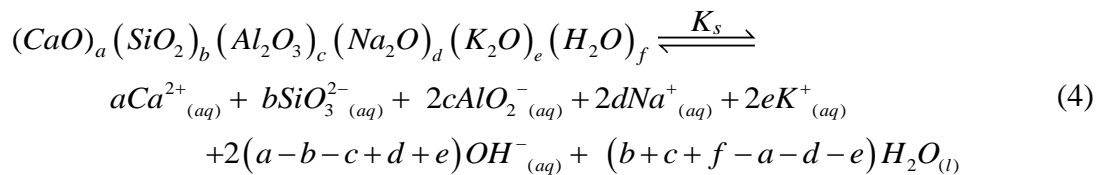

where  $a$ ,  $b$ ,  $c$ ,  $d$ ,  $e$  and  $f$  are the respective stoichiometric coefficients for CaO, SiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, Na<sub>2</sub>O, K<sub>2</sub>O and H<sub>2</sub>O in C-(N,K-)A-S-H. This reaction implies the following relationship for  $K_s$  (eq.(6)):

$$K_s = \{Ca^{2+}_{(aq)}\}^a \cdot \{SiO_3^{2-}_{(aq)}\}^b \cdot \{AlO_2^{-}_{(aq)}\}^{2c} \cdot \{Na^{+}_{(aq)}\}^{2d} \cdot \{K^{+}_{(aq)}\}^{2e} \cdot \{OH^{-}_{(aq)}\}^{2(a-b-c+d+e)} \cdot \{H_2O_{(l)}\}^{(b+c+f-a-d-e)} \quad (4)$$

Activities of  $\text{Ca}^{2+}_{(\text{aq})}$ ,  $\text{SiO}_3^{2-}_{(\text{aq})}$ ,  $\text{AlO}_2^{-}_{(\text{aq})}$ ,  $\text{Na}^{+}_{(\text{aq})}$ ,  $\text{K}^{+}_{(\text{aq})}$ ,  $\text{OH}^{-}_{(\text{aq})}$  and  $\text{H}_2\text{O}_{(\text{l})}$  species were calculated with GEM-Selektor v.3,<sup>38, 39</sup> using the measured concentrations of Ca, Si, Al, Na, K and  $\text{OH}^{-}$  in the supernatants.

### 3. Results and discussion

#### 3.1 Solid phase analysis

The XRD results (Figure 2) show that the main solid phase formed in each of the Al-free samples is C-(N,K-)S-H (phase quantification is presented as Electronic Supporting Information, Appendix S3). This is the only reaction product identified in the samples synthesised with Ca/Si\* ratios of 0.6 and 1 by XRD and TGA (Electronic Supporting Information, Appendix S4). Reflections assigned to portlandite ( $\text{Ca}(\text{OH})_2$ , Powder Diffraction File (PDF)# 00-044-1481) are only present in the data for the Al-free sample synthesised with 0.5 M NaOH/0.5 M KOH at a Ca/Si\* ratio of 1.4, although portlandite is also identified in some other Al-free samples synthesised with alkali hydroxide solutions and Ca/Si\* ratios  $\geq 1.2$ . Portlandite has been observed in C-(N,K-)S-H samples cured for 3 weeks or longer at 25°C with Ca/Si\* ratios  $> 1$  and  $[\text{NaOH}] \geq 1 \text{ M}$ ,<sup>9, 23</sup> in good agreement with these results. Calcite ( $\text{CaCO}_3$ , PDF# 00-005-0586), aragonite ( $\text{CaCO}_3$ , PDF# 00-041-1475), natrite ( $\text{Na}_2\text{CO}_3$ , PDF# 01-075-6816), thermonatrite ( $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$ , PDF# 00-005-0586) and trona ( $\text{Na}_3\text{H}(\text{CO}_3)_2 \cdot 2\text{H}_2\text{O}$ , PDF# 01-078-1064) are present in some of the samples, formed by superficial carbonation during preparation and/or analysis.

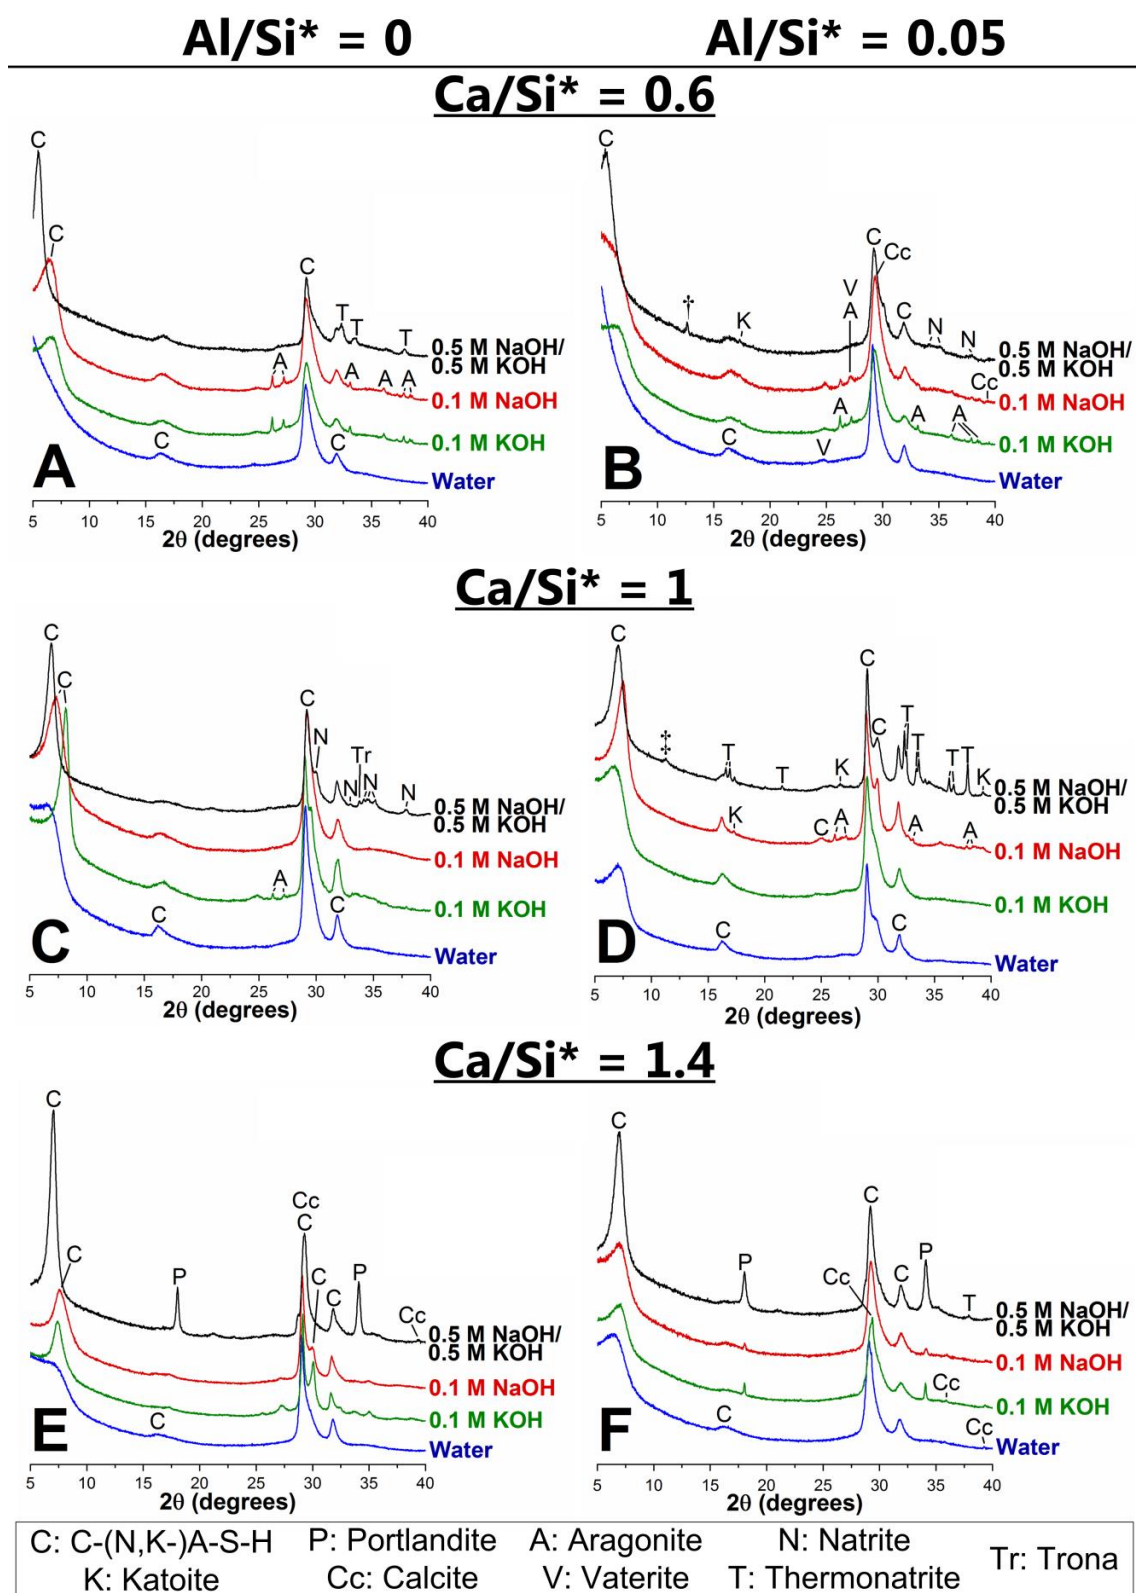


Figure 2. Cu K $\alpha$  diffractograms of C-(N,K)-A-S-H samples equilibrated at 50°C: A) Ca/Si\* = 0.6 and Al/Si\* = 0; B) Ca/Si\* = 0.6 and Al/Si\* = 0.05; C) Ca/Si\* = 1 and Al/Si\* = 0; D) Ca/Si\* = 1 and Al/Si\* = 0.05; E) Ca/Si\* = 1.4 and Al/Si\* = 0; and F) Ca/Si\* = 1.4 and Al/Si\* = 0.05. The peaks marked by † and ‡ are tentatively assigned to K-natrolite and carbonated calcium hemicarboaluminate hydrate. Ca/Si\* = bulk Ca/Si. Al/Si\* = bulk Al/Si.

The solid reaction products identified in the C-(N,K-)A-S-H samples with  $\text{Al/Si}^* = 0.05$  are similar to those identified in their Al-free counterparts: the main reaction product in each specimen is C-(N,K-)A-S-H, and portlandite is only identified in samples synthesised with 0.1 M and 1 M alkali hydroxide solutions at  $\text{Ca/Si}^*$  ratios  $\geq 1.2$  (Figure 2). Katoite  $((\text{CaO})_3(\text{Al}_2\text{O}_3)(\text{H}_2\text{O})_6)$ , PDF# 00-024-0217) is additionally present in some samples, although only in minor amounts ( $\leq 2$  wt.% of the total sample mass). The superficial carbonation products calcite, aragonite, vaterite ( $\text{CaCO}_3$ , PDF# 04-015-9018), natrite and thermonatrite are identified in some of the Al-containing samples. These phase assemblages are similar to those identified by XRD in C-(N,K-)A-S-H samples synthesised using the same method and bulk chemical compositions but at  $20^\circ\text{C}$ .<sup>8</sup> The small peaks at  $12.6^\circ 2\theta$  and  $11.3^\circ 2\theta$  in the diffractograms of the  $\text{Ca/Si}^* = 0.6$  and  $\text{Ca/Si}^* = 1$  samples synthesised with 0.5 M NaOH/0.5 M KOH are tentatively assigned to K-natrolite (PDF# 01-080-0519)<sup>53</sup> and carbonated calcium hemicarboaluminate hydrate ( $0.125 < \text{C/Ca} < 0.25$ ),<sup>54</sup> respectively.

The C-(N,K-)A-S-H products in the alkali-containing samples are much more crystalline than the specimen prepared in the absence of alkalis, as identified by the much clearer and sharper (002) reflections between  $5$  and  $10^\circ 2\theta$  in the presence of Na and/or K (Figure 2). The effects of C-(N,K-)A-S-H chemical composition and alkali hydroxide concentration on the (002) reflections are presented in section 3.3 below.

### 3.2 Aqueous phase analysis

The measured concentrations of Si, Ca and  $\text{OH}^-$  in the supernatants of the C-(N,K-)A-S-H samples do not change greatly as a function of the bulk Al concentration (Figure 3). In general, the measured aqueous Si and  $\text{OH}^-$  concentrations are higher and the dissolved Ca

concentrations are lower in samples synthesised with solutions containing more alkalis. The aqueous Si concentrations typically decrease and the dissolved Ca concentrations generally increase as functions of the Ca/Si\* ratio. The OH<sup>-</sup> concentrations are generally greater and less dependent on chemical composition at higher bulk Ca content. These results are consistent with existing solubility measurements in the CaO-(Na<sub>2</sub>O,K<sub>2</sub>O)-Al<sub>2</sub>O<sub>3</sub>-SiO<sub>2</sub>-H<sub>2</sub>O systems at ~25°C,<sup>21-24, 35, 55, 56</sup> which show the same trends in dissolved Si, Ca and OH<sup>-</sup> concentrations with respect to the bulk alkali content and Ca/Si ratio. Here, dissolved Al concentrations were generally found to be lower at higher Ca/Si\* ratios, and higher in samples more highly concentrated in alkalis.

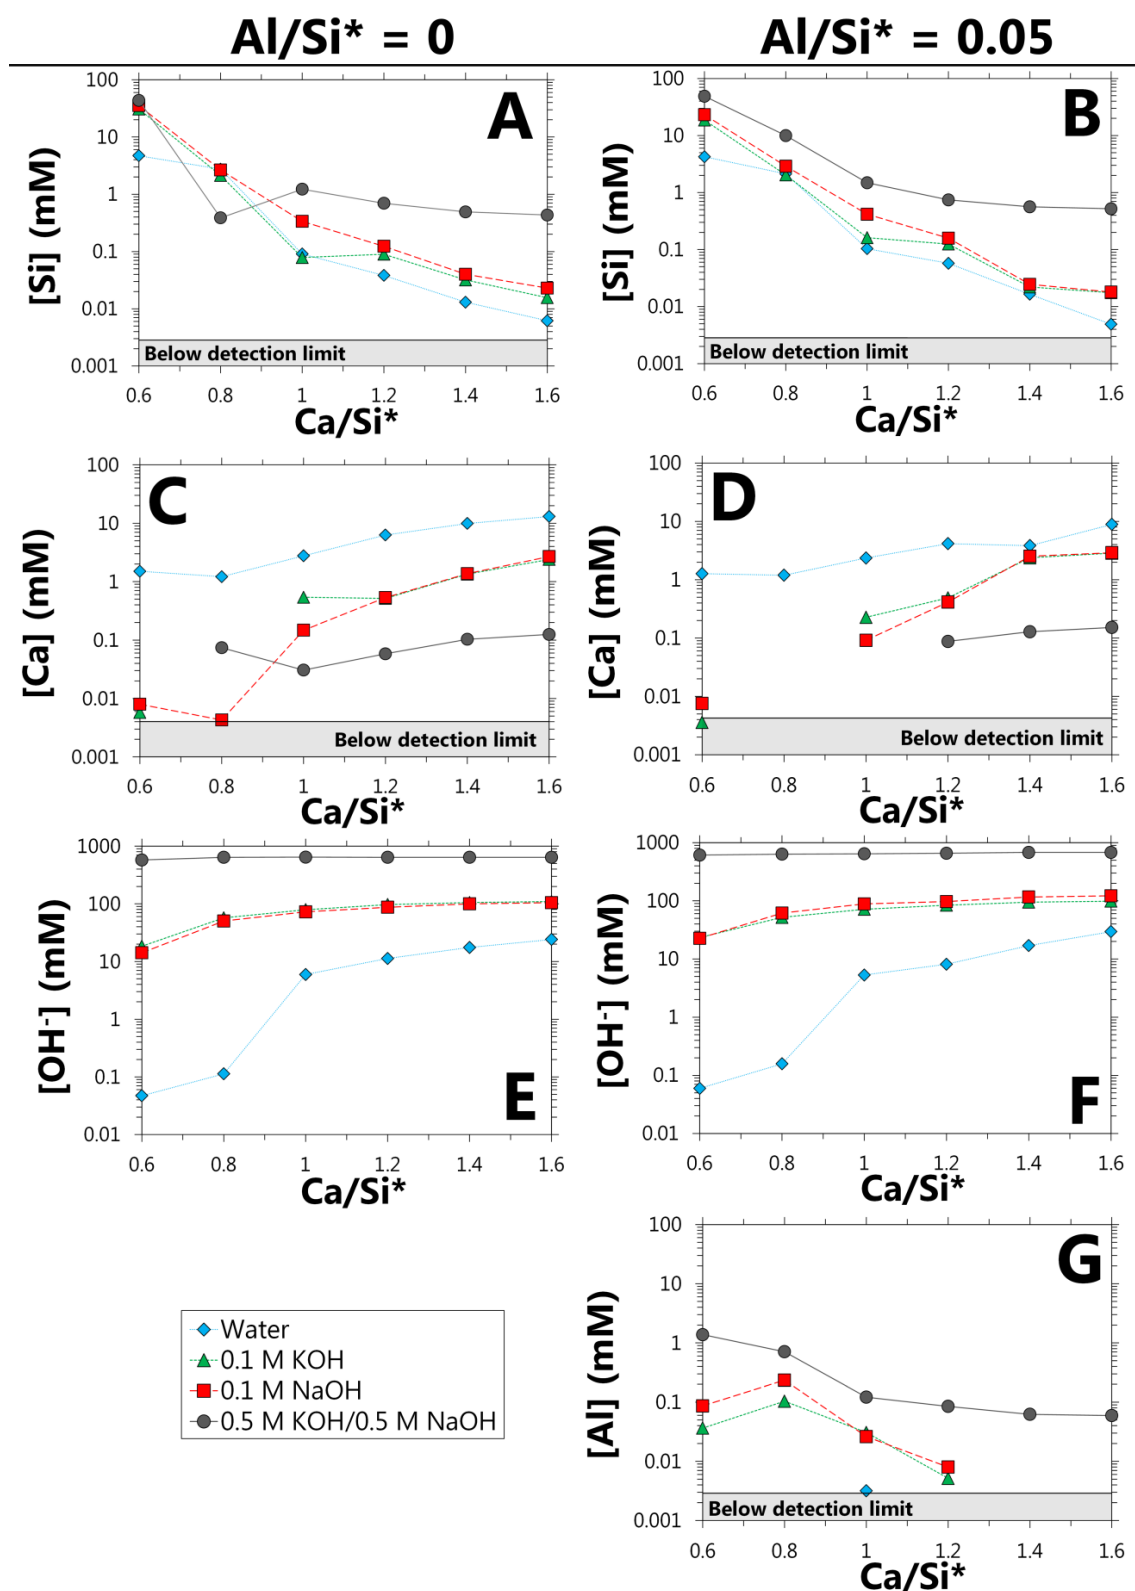


Figure 3. Concentrations of dissolved Si, Ca, OH<sup>-</sup> and Al in the supernatants of the C-(N,K-)A-S-H samples: A) [Si], Al/Si\* = 0; B) [Si], Al/Si\* = 0.05; C) [Ca], Al/Si\* = 0; D) [Ca], Al/Si\* = 0.05; E) [OH<sup>-</sup>], Al/Si\* = 0; F) [OH<sup>-</sup>], Al/Si\* = 0.05; G) [Al], Al/Si\* = 0.05. OH<sup>-</sup> concentrations are calculated from pH measurements at ~24°C. The estimated relative uncertainty of the IC measurements is ±10%. Ca/Si\* = bulk Ca/Si. Al/Si\* = bulk Al/Si. Lines are for eye-guides only. These results are tabulated in Appendix S6 (Electronic Supporting Information).

Dissolved Si, Ca and OH<sup>-</sup> concentrations in the sample sets synthesised with 0.1 M KOH and with 0.1 M NaOH are equal for Ca/Si\*  $\geq$  1.2, and are also similar for most samples with lower Ca content (Figure 3). This result suggests that C-(N,K-)A-S-H solubility does not vary greatly as a function of the nature of the alkali cation (Na or K) present. However, the large changes in dissolved Si, Ca, OH<sup>-</sup> and Al concentrations as functions of the bulk alkali concentration and the Ca/Si ratio indicate that C-(N,K-)A-S-H solubility may change significantly with respect to these parameters, as will be discussed further in section 3.4. Saturation indices calculated using the measured aqueous Si, Ca, OH<sup>-</sup> and Al concentrations shown in Figure 3 indicate that the samples containing katoite (*e.g.* the Ca/Si\* = 1, Al/Si\* = 0.05, 0.5 M NaOH/0.5 M KOH sample, see Figure 2) did not reach equilibrium within the experimental timeframe here, as this phase is calculated to be undersaturated in the systems analysed. There was otherwise good agreement between the phase assemblages formed and the calculated saturation indices. These results are presented in detail as Electronic Supporting Information (Appendix S5).

### **3.3 C-(N,K-)A-S-H chemical composition and basal spacing**

Chemical compositions of the C-(N,K-)A-S-H products formed at Al/Si\* ratios = 0 and 0.05 are shown in Tables 1 and 2. Most of the C-(N,K-)A-S-H products formed at  $0.6 \leq \text{Ca/Si}^*$  ratios  $\leq$  1.4 have Ca/Si and Al/Si ratios similar to the bulk synthesis conditions used in the samples synthesised with water and 0.1 M alkali solutions, due to the relatively low levels of secondary or superficial carbonation products formed in these specimen (yield is  $\geq$ 91 wt.% C-(N,K-)A-S-H in these samples; Appendix S3, Electronic Supporting Information). Samples synthesised with Ca/Si\* ratios = 1.6 and alkali hydroxide solutions contain more portlandite due to the decreased solubility of this phase at higher Ca and alkali content (Tables 1 and 2).



Table 1. Chemical compositions of the C-(N,K-)S-H products ( $\text{Al/Si}^* = 0$ ), determined from Rietveld analysis and IC, TGA, XRD and pH measurements (normal font), and from IC, TGA and pH measurements considering C-(N,K-)S-H and portlandite only (italic font). The estimated absolute errors are  $\pm 0.05$  units in the  $\text{Ca}/(\text{Al}+\text{Si})$  ratios,  $\pm 0.2$  units in the  $\text{H}_2\text{O}/(\text{Al}+\text{Si})$  ratios, and  $\pm 0.08$  units for the 0.1 M alkali samples and  $\pm 0.7$  for the 1 M alkali samples in the  $(\text{Na}+\text{K})/(\text{Al}+\text{Si})$  ratios of the C-(N,K-)S-H products.  $\text{Ca/Si}^* = \text{bulk Ca/Si}$ .

Synthesis solution	C-(N,K-)S-H chemical formula	Ca/Si	Na/Si	K/Si	H <sub>2</sub> O/Si
<b>Ca/Si* = 0.6</b>					
Water	$(\text{CaO})_{0.61}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.1}$	0.61	n/a <sup>a</sup>	n/a <sup>b</sup>	1.1
0.1 M NaOH	$(\text{CaO})_{0.70}(\text{Na}_2\text{O})_{0.11}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.6}$	0.70	0.23	n/a <sup>b</sup>	1.6
0.1 M KOH	$(\text{CaO})_{0.69}(\text{K}_2\text{O})_{0.13}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.6}$	0.69	n/a <sup>a</sup>	0.27	1.6
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{0.73}(\text{Na}_2\text{O})_{0.04}(\text{K}_2\text{O})_{0.08}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.7}$	0.73	0.08	0.16	1.7
<b>Ca/Si* = 0.8</b>					
Water	$(\text{CaO})_{0.80}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.9}$	0.80	n/a <sup>a</sup>	n/a <sup>b</sup>	1.9
0.1 M NaOH	$(\text{CaO})_{0.81}(\text{Na}_2\text{O})_{0.09}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.5}$	0.81	0.18	n/a <sup>b</sup>	1.5
0.1 M KOH	$(\text{CaO})_{0.81}(\text{K}_2\text{O})_{0.10}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.3}$	0.81	n/a <sup>a</sup>	0.21	1.3
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{0.3}(\text{Na}_2\text{O})_{0.02}(\text{K}_2\text{O})_{0.02}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.1}$ <sup>c</sup>	0.30 <sup>c</sup>	0.03 <sup>c</sup>	0.04 <sup>c</sup>	1.1 <sup>c</sup>
<b>Ca/Si* = 1</b>					
Water	$(\text{CaO})_{1.0}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.4}$	1.0	n/a <sup>a</sup>	n/a <sup>b</sup>	1.4
0.1 M NaOH	$(\text{CaO})_{1.0}(\text{Na}_2\text{O})_{0.06}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.3}$	1.0	0.12	n/a <sup>b</sup>	1.3
0.1 M KOH	$(\text{CaO})_{1.0}(\text{K}_2\text{O})_{0.07}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.6}$	1.0	n/a <sup>a</sup>	0.13	1.6
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{1.0}(\text{Na}_2\text{O})_{0.07}(\text{K}_2\text{O})_{0.08}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.7}$	1.0	0.15	0.17	1.7
<b>Ca/Si* = 1.2</b>					
Water	$(\text{CaO})_{1.2}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.5}$	1.2	n/a <sup>a</sup>	n/a <sup>b</sup>	1.5
0.1 M NaOH	$(\text{CaO})_{1.2}(\text{Na}_2\text{O})_{0.02}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.4}$	1.2	0.05	n/a <sup>b</sup>	1.4
0.1 M KOH	$(\text{CaO})_{1.2}(\text{K}_2\text{O})_{0.03}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.6}$	1.2	n/a <sup>a</sup>	0.06	1.6
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{1.0}(\text{Na}_2\text{O})_{0.09}(\text{K}_2\text{O})_{0.08}(\text{SiO}_2)_1(\text{H}_2\text{O})_{2.0}$	1.0	0.19	0.16	2.0
<b>Ca/Si* = 1.4</b>					
Water	$(\text{CaO})_{1.3}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.9}$	1.3	n/a <sup>a</sup>	n/a <sup>b</sup>	1.9
0.1 M NaOH	$(\text{CaO})_{1.4}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.7}$	1.4	<0.01	n/a <sup>b</sup>	1.7
0.1 M KOH	$(\text{CaO})_{1.4}(\text{K}_2\text{O})_{0.02}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.9}$	1.4	n/a <sup>a</sup>	0.03	1.9
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{1.4}(\text{Na}_2\text{O})_{0.09}(\text{K}_2\text{O})_{0.08}(\text{SiO}_2)_1(\text{H}_2\text{O})_{2.1}$	1.4	0.18	0.16	2.1

302

Table 1. Continued.

<b>Ca/Si* = 1.6</b>					
Water	$(CaO)_{1.5}(SiO_2)_1(H_2O)_{2.0}$	1.5	$n/a^a$	$n/a^b$	2.0
0.1 M NaOH	$(CaO)_{1.4}(SiO_2)_1(H_2O)_{1.8}$	1.4	<0.01	$n/a^b$	1.8
0.1 M KOH	$(CaO)_{1.4}(K_2O)_{0.01}(SiO_2)_1(H_2O)_{1.7}$	1.4	$n/a^a$	0.02	1.7
0.5 M NaOH/0.5 M KOH	$(CaO)_{1.3}(SiO_2)_1(H_2O)_{1.1}$	1.3	<0.01	<0.01	1.1

303 <sup>a</sup> n/a = not applicable: no Na was added during synthesis (<0.6 mM Na is present as an impurity in the 0.1 M KOH synthesis solution).

304 <sup>b</sup> n/a = not applicable: no K was added during synthesis.

305 <sup>c</sup> An additional major phase, possibly a zeolite, was formed in this sample in addition to C-(N,K-)S-H.

306 Table 2. Chemical compositions of the C-(N,K-)A-S-H products ( $\text{Al/Si}^* = 0.05$ ), determined from Rietveld analysis and IC, TGA, XRD and pH  
307 measurements (normal font), and from IC, TGA and pH measurements considering C-(N,K-)S-H and portlandite only (italic font). The estimated  
308 absolute errors are  $\pm 0.05$  units in the  $\text{Ca}/(\text{Al}+\text{Si})$  ratios,  $\pm 0.2$  units in the  $\text{H}_2\text{O}/(\text{Al}+\text{Si})$  ratios,  $\pm 0.02$  units in the  $\text{Al/Si}$  ratios, and  $\pm 0.08$  units for  
309 the 0.1 M alkali samples and  $\pm 0.7$  for the 1 M alkali samples in the  $(\text{Na}+\text{K})/(\text{Al}+\text{Si})$  ratios of the C-(N,K-)A-S-H products.  $\text{Ca/Si}^* = \text{bulk Ca/Si}$ .

Synthesis solution	C-(N,K-)A-S-H chemical formula	$\text{Ca}/(\text{Al}+\text{Si})$	$\text{Al/Si}$	$\text{Na}/(\text{Al}+\text{Si})$	$\text{K}/(\text{Al}+\text{Si})$	$\text{H}_2\text{O}/(\text{Al}+\text{Si})$
<b><math>\text{Ca/Si}^* = 0.6</math></b>						
Water	$(\text{CaO})_{0.60}(\text{Al}_2\text{O}_3)_{0.026}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.4}$	0.57	0.051	n/a <sup>a</sup>	n/a <sup>b</sup>	1.3
0.1 M NaOH	$(\text{CaO})_{0.66}(\text{Al}_2\text{O}_3)_{0.28}(\text{Na}_2\text{O})_{0.13}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.7}$	0.63	0.055	0.25	n/a <sup>b</sup>	1.6
0.1 M KOH	$(\text{CaO})_{0.65}(\text{Al}_2\text{O}_3)_{0.027}(\text{K}_2\text{O})_{0.13}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.2}$	0.62	0.054	n/a <sup>a</sup>	0.24	1.1
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{0.76}(\text{Al}_2\text{O}_3)_{0.028}(\text{Na}_2\text{O})_{0.13}(\text{K}_2\text{O})_{0.13}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.9}$	0.72	0.056	0.24	0.24	1.8
<b><math>\text{Ca/Si}^* = 0.8</math></b>						
Water	$(\text{CaO})_{0.80}(\text{Al}_2\text{O}_3)_{0.025}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.7}$	0.76	0.051	n/a <sup>a</sup>	n/a <sup>b</sup>	1.6
0.1 M NaOH	$(\text{CaO})_{0.81}(\text{Al}_2\text{O}_3)_{0.25}(\text{Na}_2\text{O})_{0.11}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.4}$	0.77	0.050	0.21	n/a <sup>b</sup>	1.3
0.1 M KOH	$(\text{CaO})_{0.81}(\text{Al}_2\text{O}_3)_{0.025}(\text{K}_2\text{O})_{0.10}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.2}$	0.77	0.050	n/a <sup>a</sup>	0.19	1.1
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{0.84}(\text{Al}_2\text{O}_3)_{0.024}(\text{Na}_2\text{O})_{0.18}(\text{K}_2\text{O})_{0.17}(\text{SiO}_2)_1(\text{H}_2\text{O})_{2.8}$	0.80	0.049	0.35	0.33	2.7
<b><math>\text{Ca/Si}^* = 1</math></b>						
Water	$(\text{CaO})_{0.99}(\text{Al}_2\text{O}_3)_{0.025}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.5}$	0.94	0.050	n/a <sup>a</sup>	n/a <sup>b</sup>	1.4
0.1 M NaOH	$(\text{CaO})_{1.0}(\text{Al}_2\text{O}_3)_{0.023}(\text{Na}_2\text{O})_{0.06}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.3}$	1.00	0.045	0.12	n/a <sup>b</sup>	1.3
0.1 M KOH	$(\text{CaO})_{1.0}(\text{Al}_2\text{O}_3)_{0.025}(\text{K}_2\text{O})_{0.06}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.3}$	0.95	0.050	n/a <sup>a</sup>	0.11	1.3
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{1.0}(\text{Al}_2\text{O}_3)_{0.025}(\text{Na}_2\text{O})_{0.13}(\text{K}_2\text{O})_{0.10}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.8}$	0.96	0.050	0.25	0.20	1.7
<b><math>\text{Ca/Si}^* = 1.2</math></b>						
Water	$(\text{CaO})_{1.2}(\text{Al}_2\text{O}_3)_{0.025}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.8}$	1.12	0.050	n/a <sup>a</sup>	n/a <sup>b</sup>	1.7
0.1 M NaOH	$(\text{CaO})_{1.2}(\text{Al}_2\text{O}_3)_{0.025}(\text{Na}_2\text{O})_{0.04}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.5}$	1.14	0.050	0.08	n/a <sup>b</sup>	1.4
0.1 M KOH	$(\text{CaO})_{1.2}(\text{Al}_2\text{O}_3)_{0.025}(\text{K}_2\text{O})_{0.02}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.4}$	1.14	0.050	n/a <sup>a</sup>	0.04	1.4
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{1.0}(\text{Al}_2\text{O}_3)_{0.025}(\text{Na}_2\text{O})_{0.14}(\text{K}_2\text{O})_{0.10}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.8}$	0.99	0.050	0.26	0.20	1.7
<b><math>\text{Ca/Si}^* = 1.4</math></b>						
Water	$(\text{CaO})_{1.4}(\text{Al}_2\text{O}_3)_{0.025}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.9}$	1.3	0.050	n/a <sup>a</sup>	n/a <sup>b</sup>	1.8
0.1 M NaOH	$(\text{CaO})_{1.4}(\text{Al}_2\text{O}_3)_{0.025}(\text{Na}_2\text{O})_{0.02}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.8}$	1.3	0.050	0.05	n/a <sup>b</sup>	1.8
0.1 M KOH	$(\text{CaO})_{1.4}(\text{Al}_2\text{O}_3)_{0.025}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.5}$	1.3	0.050	n/a <sup>a</sup>	<0.01	1.4
0.5 M NaOH/0.5 M KOH	$(\text{CaO})_{1.2}(\text{Al}_2\text{O}_3)_{0.025}(\text{Na}_2\text{O})_{0.12}(\text{K}_2\text{O})_{0.10}(\text{SiO}_2)_1(\text{H}_2\text{O})_{1.7}$	1.2	0.050	0.23	0.19	1.6

310

311

Table 2. Continued.

**Ca/Si\* = 1.6**

Water	$(CaO)_{1.5}(Al_2O_3)_{0.025}(SiO_2)_1(H_2O)_{2.1}$	1.5	0.050	<i>n/a</i> <sup>a</sup>	<i>n/a</i> <sup>b</sup>	2.0
0.1 M NaOH	$(CaO)_{1.3}(Al_2O_3)_{0.025}(Na_2O)_{0.02}(SiO_2)_1(H_2O)_{1.7}$	1.3	0.050	0.03	<i>n/a</i> <sup>b</sup>	1.7
0.1 M KOH	$(CaO)_{1.3}(Al_2O_3)_{0.025}(SiO_2)_1(H_2O)_{1.5}$	1.2	0.050	<i>n/a</i> <sup>a</sup>	<0.01	1.4
0.5 M NaOH/0.5 M KOH	$(CaO)_{1.2}(Al_2O_3)_{0.025}(Na_2O)_{0.15}(K_2O)_{0.12}(SiO_2)_1(H_2O)_{1.8}$	1.2	0.050	0.29	0.23	1.7

312 <sup>a</sup> n/a = not applicable: no Na was added during synthesis (<0.6 mM Na is present as an impurity in the 0.1 M KOH synthesis solution).

313 <sup>b</sup> n/a = not applicable: no K was added during synthesis.

314

The C-(N,K-)A-S-H products typically contain  $H_2O/(Al+Si)$  ratios between 1 and 2 (Figure 4): the  $H_2O$  content in C-(N,K-)A-S-H was determined by assigning the mass losses between 30°C and 550°C to the decomposition of C-(N,K-)A-S-H, portlandite, katoite and  $Al(OH)_3$  during heating by TGA (Appendix S4, Electronic Supporting Information). Portlandite was the only secondary product quantified by TGA and used in C-(N,K-)A-S-H chemical composition calculations in the absence of XRD data; the formation of only very small quantities of other secondary products here ( $\leq 2$  wt.% of the total mass of each sample) means that any errors introduced into the reported C-(N,K-)A-S-H chemical compositions due to use of this method are minor.

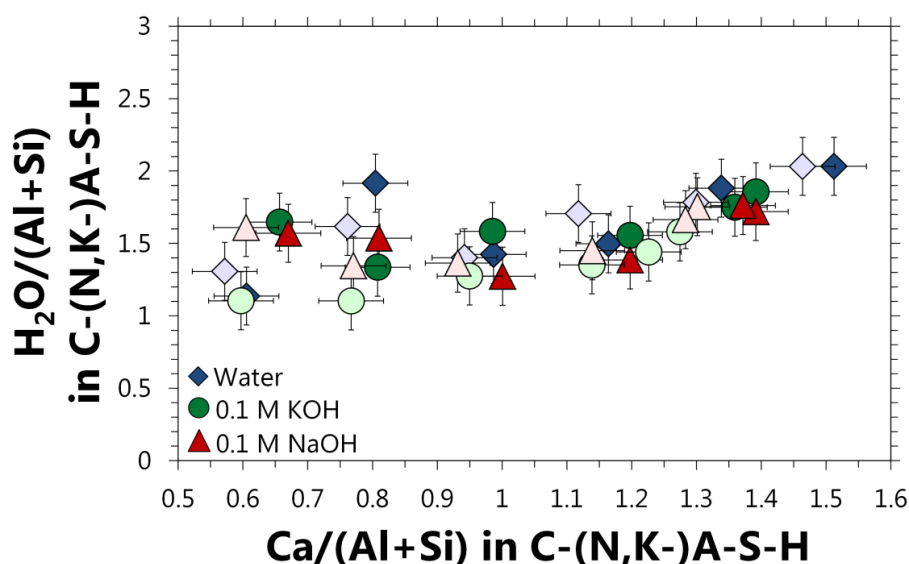


Figure 4.  $H_2O/(Al+Si)$  ratios of the ( $Al/Si^* = 0$ ) C-(N,K-)S-H (dark symbols) and  $Al/Si^* = 0.05$  C-(N,K-)A-S-H (light symbols) as functions of the  $Ca/(Al+Si)$  ratio, for samples synthesised with  $\leq 0.1$  M alkali hydroxide solutions and equilibrated at 50°C. The estimated absolute errors are  $\pm 0.05$  units in the  $Ca/(Al+Si)$  ratios and  $\pm 0.2$  in the  $H_2O/(Al+Si)$  ratios of the C-(N,K-)A-S-H products.

The reported  $H_2O/(Al+Si)$  ratios (Figure 4) are in relatively good agreement with the expected result for C-(N,K-)A-S-H equilibrated at  $\sim 30\%$  RH, where no ‘free’ water is present and some adsorbed water is removed,<sup>57, 58</sup> and with the  $H_2O$  content of C-(N,K-)A-S-H synthesised at 20°C.<sup>8</sup> In general, the  $H_2O/(Al+Si)$  ratios increase slightly as a direct function

of the  $\text{Ca}/(\text{Al}+\text{Si})$  ratios of the C-(N,K-)A-S-H products formed, but no significant correlations are found between the  $\text{H}_2\text{O}/(\text{Al}+\text{Si})$  ratio and the alkali or Al content in this phase. A strong direct relationship between the  $\text{H}_2\text{O}/(\text{Al}+\text{Si})$  and  $\text{Ca}/(\text{Al}+\text{Si})$  ratios is reported for laboratory-synthesised C-S-H,<sup>59</sup> but is not as evident here from the data in presented in Figure 4. Chemical compositions of the C-(N,K-)A-S-H products synthesised using 0.5 M NaOH/0.5 KOH solutions are omitted from Figure 4 due to the relatively higher quantities of secondary products formed in these samples.

The alkali and Al contents of the C-(N,K-)A-S-H products formed are independent of each other when relatively low amounts of Al are present (comparing the darker-coloured symbols with  $\text{Al}/\text{Si}^* = 0$  to the lighter-coloured symbols with  $\text{Al}/\text{Si}^* = 0.05$  in Figure 5). At  $\text{Al}/\text{Si}^*$  ratios  $\leq 0.05$ , all of the Al added is generally incorporated into C-(N,K-)A-S-H products when synthesised with water and no added alkalis (Table 2).<sup>14</sup> However, the amount of Al which can be incorporated into C-(N,K-)A-S-H is related to the dissolved concentration of this element at higher bulk Al content: increasing the bulk Na or K concentration increases the amount of dissolved Al (Figure 3) and consequently also the amount of Al which can be incorporated into C-(N,K-)A-S-H.<sup>8</sup> This description is consistent with <sup>29</sup>Si MAS NMR analysis of hydrated white Portland cement with different alkali contents,<sup>33</sup> which showed the formation of C-(N,K-)A-S-H products with increased Al/Si ratios at higher bulk alkali concentration. This description is also in agreement with the lack of a direct relationship found in <sup>11</sup> between alkali and Al content in laboratory-synthesised C-(N,K-)S-H, and in C-(N,K-)A-S-H with  $\text{Al}/\text{Si} = 0.04$  in hydrated blends of PC and silica fume.

The amount of Na and K incorporated in the C-(N,K-)A-S-H products decreases with the  $\text{Ca}/(\text{Al}+\text{Si})$  ratio of this phase (Figure 5), from  $(\text{Na}+\text{K})/(\text{Al}+\text{Si}) = 0.25$  at  $\text{Ca}/(\text{Al}+\text{Si}) = 0.6$  to

zero Na and K incorporated at  $\text{Ca}/(\text{Al}+\text{Si}) = 1.6$ . This trend, and the quantified  $(\text{Na}+\text{K})/(\text{Al}+\text{Si})$  ratios, are consistent with those reported in earlier studies of alkali uptake in laboratory-synthesised C-(N,K-)A-S-H at room temperature.<sup>21, 25, 34, 60</sup> The  $(\text{Na}+\text{K})/(\text{Al}+\text{Si})$  ratios of the C-(N,K-)A-S-H products are independent of the nature of the alkali element (Na or K).

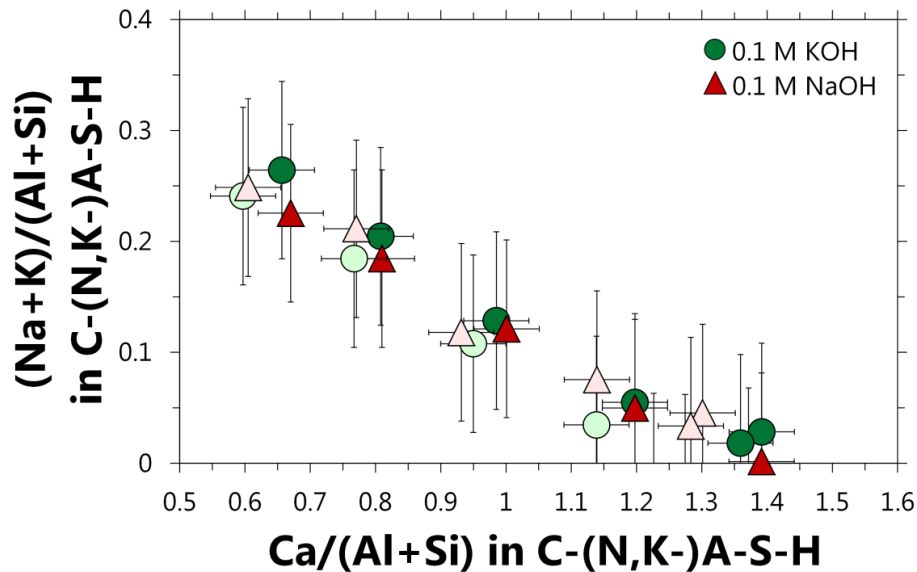


Figure 5. Alkali cation uptake in C-(N,K-)S-H ( $\text{Al}/\text{Si}^* = 0$ , dark symbols) and  $\text{Al}/\text{Si}^* = 0.05$  C-(N,K-)A-S-H (light symbols) as functions of the  $\text{Ca}/(\text{Al}+\text{Si})$  ratio, for samples synthesised with 0.1 M alkali hydroxide solutions at 50°C. The estimated absolute errors are  $\pm 0.05$  units in the  $\text{Ca}/(\text{Al}+\text{Si})$  ratios and  $\pm 0.08$  units in the  $(\text{Na}+\text{K})/(\text{Al}+\text{Si})$  ratios of the C-(N,K-)A-S-H products.

The increased alkali uptake determined here for C-(N,K-)A-S-H with lower  $\text{Ca}/(\text{Al}+\text{Si})$  ratios (Figure 5) is explained here in terms of the incorporation of more alkali in C-(N,K-)A-S-H interlayer spaces at lower Ca content. This explanation is consistent with the largest basal spacings measured here at the lowest  $\text{Ca}/(\text{Al}+\text{Si})$  ratios, at a fixed alkali hydroxide concentration (Figure 6). An inverse relationship between basal spacing and  $\text{Ca}/(\text{Al}+\text{Si})$  ratio has also been reported for alkali-free calcium silicate hydrate<sup>61</sup> and alkali-free calcium aluminosilicate hydrate (C-A-S-H) with  $\text{Ca}/(\text{Al}+\text{Si})$  ratios  $< 1$ .<sup>62</sup>

The positions of the (002) reflections in Figure 6 correspond to average basal spacings of 10.8-16 Å for the C-(N,K-)S-H products ( $\text{Al/Si}^* = 0$ ) and average basal spacings of 11.7-16.1 Å for the C-(N,K-)A-S-H products ( $\text{Al/Si}^* = 0.05$ ). In addition to the incorporation of alkali in C-(N,K-)A-S-H interlayer spaces, this variation in basal spacing is also explained by the assignment of the C-(N,K-)A-S-H products formed to poorly-ordered structural analogues of orthorhombic 14 Å tobermorite (PDF# 00-029-0331), 11 Å tobermorite (PDF# 04-017-1028), 9 Å tobermorite (PDF# 04-012-1761), a mixture of these minerals,<sup>61</sup> or monoclinic clinotobermorite (PDF# 01-088-1328).<sup>59</sup>

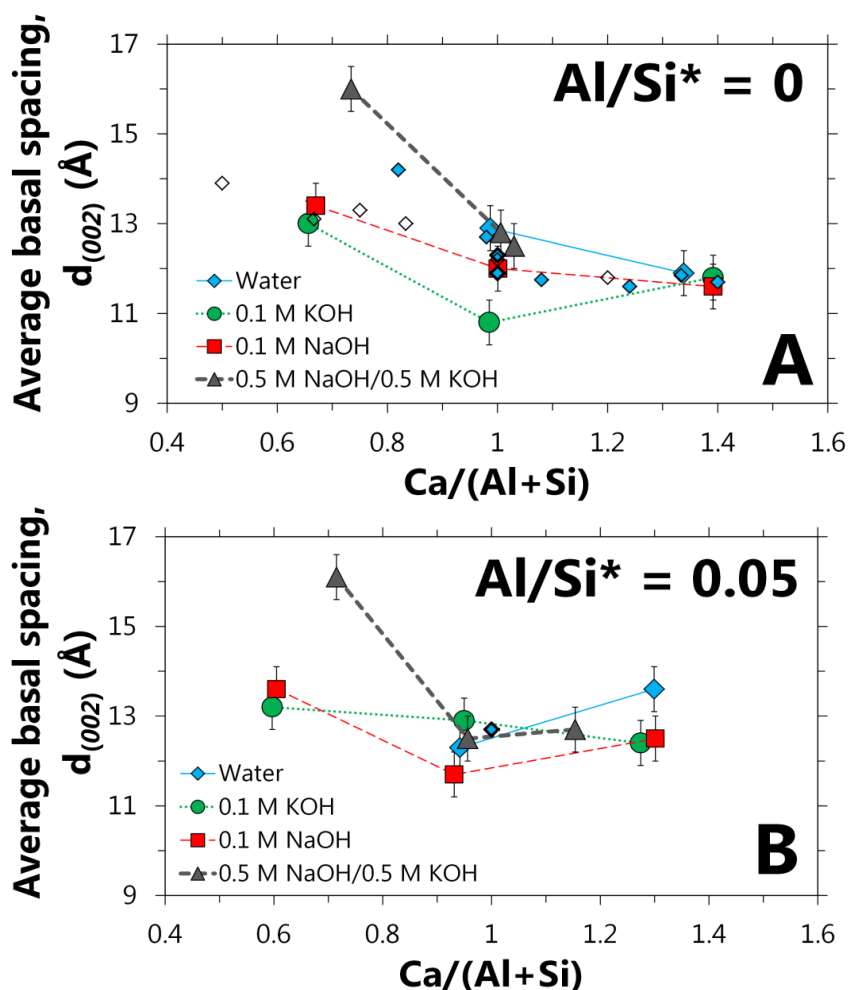


Figure 6. Average ( $d_{(002)}$ ) basal spacings (estimated uncertainty =  $\pm 0.5$  Å) of the C-(N,K-)A-S-H products synthesised with A)  $\text{Al/Si}^* = 0$  and B)  $\text{Al/Si}^* = 0.05$  (large symbols). Small bold filled diamonds are data from samples equilibrated at 20°C in <sup>8</sup>, small filled diamonds are data for 21-day old samples from <sup>62</sup>, and small open diamonds are data from <sup>63</sup>.  $\text{Al/Si}^*$  represents the bulk Al/Si ratio.



398

399 For the C-(N,K-)S-H samples ( $\text{Al/Si}^* = 0$ ), larger basal spacings are apparent in the water-  
400 synthesised specimen than in some of the alkali-containing specimens (Figure 6A). Bach et  
401 al.<sup>11</sup> reported the same trend for C-(N,K-)S-H synthesised at bulk  $[\text{NaOH}] < 0.03$  M. Here,  
402 the XRD results suggest that Na and K species are incorporated in C-(N,K-)S-H interlayers at  
403 alkali concentrations  $\geq 0.1$  M, *i.e.* more aqueous Na and/or K species are incorporated into  
404 interlayer spaces at higher Na and/or K content. The reduced basal spacings generally found  
405 for the samples synthesised with 0.1 M alkali hydroxide solutions relative to the water  
406 synthesised specimens can be attributed in part to exchange of interlayer  $\text{Ca}^{2+}$  with  $\text{K}^+$  and/or  
407  $\text{Na}^+$  (hydrated ionic radii of  $\text{Ca}^{2+} = 4.12$  Å,  $\text{K}^+ = 3.31$  Å and  $\text{Na}^+ = 3.58$  Å<sup>64</sup>). The  
408 comparatively large differences in basal spacings between these samples indicate that other  
409 factors, *e.g.* variations in the adsorbed interlayer water content, layer stacking configuration  
410 and chain lengths of the C-(N,K-)A-S-H phases formed,<sup>59</sup> are also likely to be important.

411

412 A clear relationship between  $d_{(002)}$  and Al content is not observed in Figure 6. However, basal  
413 spacings for Al-containing C-(N,K-)A-S-H were measured to be 2-3 Å greater than their Al-  
414 free counterparts at 20°C,<sup>60, 62</sup> in contrast with these results. A clear trend in  $d_{(002)}$  as a  
415 function of the bulk alkali concentration is only identifiable at  $\text{Ca/Si}^* = 0.6$  for the Al-  
416 containing samples; the largest basal spacing is identified in the sample synthesised with 0.5  
417 M NaOH/0.5 M KOH ( $d_{(002)} = 16.1$  Å). This increase in basal spacing is again explained by  
418 higher concentrations of alkali species in C-(N,K-)A-S-H interlayers at higher alkali content.

419

### 3.4 C-(N,K-)A-S-H solubility

Solubility products are calculated using eqs.(5-6) for C-(N,K-)A-S-H with hypothetical chemical compositions of  $\text{Ca}/(\text{Al}+\text{Si}) = 0.6, 0.8, 1, 1.2, 1.4$  and  $1.6$ ,  $\text{Al}/\text{Si} = 0$  and  $0.05$ ,  $\text{Na}/(\text{Al}+\text{Si}) = 0.2$  for samples containing Na,  $\text{K}/(\text{Al}+\text{Si}) = 0.2$  for samples containing K,  $\text{H}_2\text{O}/\text{Si} = 1.2$ , and  $1 \text{ mol Al} + \text{Si}$ , and shown in Figure 7. These  $\text{Na}/(\text{Al}+\text{Si})$  and  $\text{K}/(\text{Al}+\text{Si})$  ratios were chosen to approximate the alkali contents of the experimental C-(N,K-)A-S-H products (Tables 1 and 2). Hypothetical chemical compositions were chosen to enable a more direct comparison of the calculated solubility products as a function of Na, K and Al content. Solubility products for C-(N,K-)A-S-H with chemical compositions determined by mass balances from the XRD (Figure 2), IC and pH measurements (Figure 3), and TGA and Rietveld analysis (Appendices S3 and S4, Electronic Supporting Information), are shown in Appendix S6 (Electronic Supporting Information).

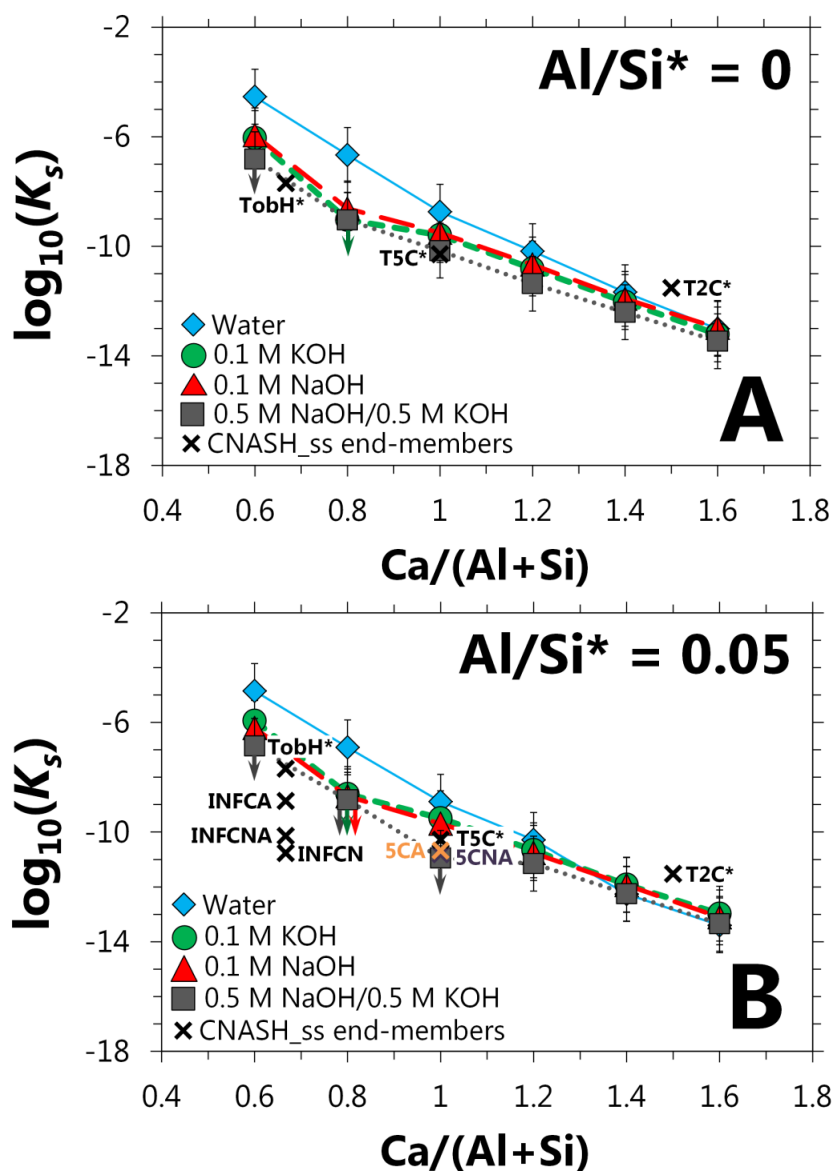


Figure 7. Solubility products ( $K_s$ ) for hypothetical C-(N,K-)A-S-H phases with chemical compositions of A)  $\text{Al}/\text{Si} = 0$  or B)  $\text{Al}/\text{Si} = 0.05$ ,  $\text{Na}/(\text{Al}+\text{Si}) = 0.2$  for the Na-containing systems,  $\text{K}/(\text{Al}+\text{Si}) = 0.2$  for the K-containing systems,  $\text{H}_2\text{O}/\text{Si} = 1.2$ , and normalised to 1 mol Al + Si at 50°C. The estimated uncertainty depicted as error bars is  $\pm 1$  unit in the  $\log_{10}(K_s)$  values, except for the points with downward-pointing arrows, which additionally represent maximum solubility product values as described in the text. The small crosses are solubility products for end-members of the CNASH\_ss thermodynamic model<sup>28</sup> at 50°C.  $\text{Al}/\text{Si}^* = \text{bulk Al}/\text{Si}$ . Lines are for eye-guides only.

Figure 7 shows similar values and trends in the solubility products for both the Al-free and Al-containing C-(N,K-)A-S-H end-members, *i.e.*, the results of this study indicate that this phase is not greatly stabilised by the incorporation of Al. This is consistent with recently published results for C-(A-)S-H synthesised with  $\text{Ca}/\text{Si}^* = 1$  and cured at 7-80°C,<sup>14</sup> where the

measured solubility of this phase did not change greatly between Al/Si\* ratios of 0 and 0.15. The downward-pointing arrows in Figure 7 for the Ca/Si\* = 0.6 and 1 C-(N,K-)A-S-H samples synthesised with 0.5 M NaOH/0.5 M KOH, and the Ca/Si\* = 0.8 samples synthesised with alkali hydroxide solutions, indicate that the calculated solubility products are considered to be upper bounds; supernatant Ca concentrations were below the detection limit for these samples, so an upper limit of [Ca] = 0.004 mM was chosen. Dissolved Al concentrations were also below the detection limit for some samples (*e.g.* the Ca/Si\* = 1.2, Al/Si\* = 0.05 sample synthesised with water, Figure 3), so [Al] = 0.003 mM was chosen for these samples. The low Al content of the C-(N,K-)A-S-H products (Al/Si ~ 0.05) means that the associated level of uncertainty in the  $K_s$  values for samples with [Al] below the detection limit is lower than for the samples with [Ca] below the detection limit; downward pointing arrows are only shown for the latter case in Figure 7.

The lower solubility products calculated for C-(N,K-)A-S-H with higher Ca/(Al+Si) ratios in Figure 7 reflect the increased amounts of Ca included in the stoichiometric formulae for C-(N,K-)A-S-H in these calculations at higher Ca/(Al+Si) ratios (Figure 7 shows solubility products for C-(N,K-)A-S-H with chemical compositions normalised to one mole Al + Si), but could additionally indicate that C-(N,K-)A-S-H is stabilised at higher Ca content within the composition range analysed here. The solubility products of the C-(N,K-)A-S-H phases synthesised using 0.1 M alkali hydroxide solutions are similar irrespective of the alkali element used, indicating that both Na- and K-bearing C-(N,K-)A-S-H can be expected to form in hydrated cements with non-zero concentrations of these alkali elements. Figure 7 also shows that C-(N,K-)A-S-H solubility generally decreases slightly as the bulk alkali hydroxide concentration is increased, but this finding is only significant for some C-(N,K-)A-S-H phases with  $\text{Ca/Si} \leq 1$ . Similar trends of decreasing solubility with increasing alkali content

are also identified in solubility product calculations for hypothetical C-(N,K-)A-S-H phases with  $(\text{Na}+\text{K})/(\text{Al}+\text{Si}) = 0$  and  $\text{Ca}/\text{Si} \leq 1$ , which suggests that the structure of this phase may be stabilised slightly as the bulk alkali concentration is increased. This will be discussed further in section 3.5.

The end-members of the CNASH<sub>ss</sub> thermodynamic model (Figure 7)<sup>28</sup> show the same trends in C-(N,K-)A-S-H solubility as identified experimentally here. The reduced solubilities of the Na-bearing end-members in the CNASH<sub>ss</sub> thermodynamic model compared to the experimental results are also consistent with their much higher Na content ( $0.4 \leq \text{Na}/(\text{Al}+\text{Si}) \leq 0.46$ ). The solubility product of the T2C\* model end-member is consistent with the experimental results, although the lower solubilities of the model T5C\*, TobH\* and INFCA end-members relative to the experimental data indicates that their thermodynamic properties should be adjusted slightly for simulations at 50°C to improve the temperature-dependent behaviour of CNASH<sub>ss</sub>.

The same method of analysis presented in sections 3.1-3.4 and shown in Figure 7 was applied to C-(N,K-)A-S-H samples with  $\text{Ca}/\text{Si}^* = 1$ ,  $\text{Al}/\text{Si}^* = 0$  and 0.1, and synthesised with water, 0.5 NaOH and 0.5 M NaOH/0.5 M KOH solutions. The solid and liquid phase analyses for these samples are presented in Appendix S7, Electronic Supporting Information, and the resulting  $K_s$  values are shown in Table 3. These data show similar trends to those described for Figure 7, *i.e.* a slight decrease in solubility as a function of increasing alkali hydroxide concentration and no significant change in solubility as a function of the  $\text{Al}/\text{Si}^*$  ratio. These results are discussed in terms of solubility-composition-structure relationships in C-(N,K-)A-S-H, using the <sup>29</sup>Si MAS NMR analysis presented for these samples, in sections 3.5-3.6 below.

Table 3. Solubility products ( $K_s$ ) for hypothetical C-(N,K-)A-S-H phases with chemical compositions of Ca/(Al+Si) = 1, Al/Si ratios = 0 (Al/Si\* = 0) or 0.1 (Al/Si\* = 0.1), Na/(Al+Si) = 0.2 for the Na-containing systems, K/(Al+Si) = 0.2 for the K-containing systems, H<sub>2</sub>O/Si = 1.2, and normalised to 1 mol Al + Si at 50°C. The estimated uncertainty is  $\pm 1$  unit in  $\log_{10}(K_s)$  values.

<b>Al/Si* = 0</b>	
Water	-8.7
0.5 M NaOH	-9.8
0.5 M NaOH/0.5 M KOH	-10.2
<b>Al/Si* = 0.1</b>	
Water	-8.9
0.5 M NaOH	-10.0
0.5 M NaOH/0.5 M KOH	$\leq -11.0^a$

<sup>a</sup> Maximum values. Activities of Ca<sup>2+</sup>, SiO<sub>3</sub><sup>2-</sup>, AlO<sub>2</sub><sup>-</sup>, Na<sup>+</sup>, K<sup>+</sup>, OH<sup>-</sup> and H<sub>2</sub>O were calculated using [Ca] = 0.004 mM, as the measured Ca concentration in the supernatant of this sample was below the detection limit.

### 3.5 <sup>29</sup>Si MAS NMR

The <sup>29</sup>Si MAS NMR spectra of the C-(N,K-)S-H samples (Al/Si\* = 0) contain three resonances, that are assigned to chain-end sites (Q<sup>1</sup>), bridging sites (Q<sup>2</sup><sub>b</sub>) and paired sites (Q<sup>2</sup><sub>p</sub>) (Figure 8A) respectively. In the spectra of the water-synthesised samples, these resonances are described by peaks located at isotropic chemical shifts ( $\delta_{\text{iso}}$ ) of -79.3 ppm, -83.1 ppm and -85.1 ppm respectively. Similar  $\delta_{\text{iso}}$  values have been reported for alkali- and Al-free C-S-H aged at 40°C.<sup>65, 66</sup> The spectrum for the Al-free sample synthesised with 0.5 M NaOH contains the same peaks but shifted by +1 to +2 ppm, which indicates that silanol groups in the 0.5 M NaOH sample are on average charge-balanced by less positively-charged species (*i.e.* Na<sup>+</sup> and/or H<sup>+</sup> rather than Ca<sup>2+</sup>) relative to the alkali-free specimen.<sup>67</sup> Comparable differences in  $\delta_{\text{iso}}$  have also been reported between the Q<sup>1</sup>, Q<sup>2</sup><sub>b</sub> and Q<sup>2</sup><sub>p</sub> sites in C-(N,K-)S-H synthesised at different alkali concentrations.<sup>8, 9</sup> The relative intensities of the Q<sup>1</sup> peaks are greatly increased in the presence of NaOH and KOH, which is discussed further in the context of a reduction in mean chain length (MCL) in section 3.6 below.

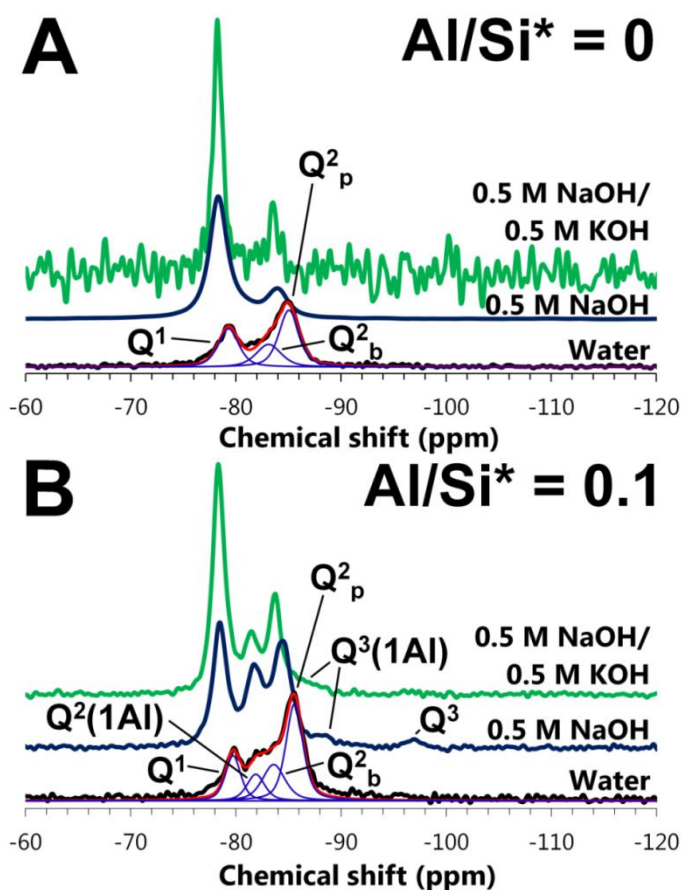


Figure 8. Solid-state  $^{29}\text{Si}$  MAS NMR spectra of A) C-(N,K-)S-H ( $\text{Al/Si}^* = 0$ ) and B) C-(N,K-)A-S-H ( $\text{Al/Si}^* = 0.1$ ) samples, synthesised with  $\text{Ca/Si}^* = 1$  and equilibrated at  $50^\circ\text{C}$ . The fits and deconvoluted peaks for the spectra of the water-synthesised samples are shown as red and blue lines respectively. Deconvolutions for each spectrum are shown in Appendix S8 (Electronic Supporting Information). The relatively high level of noise in the spectrum of the  $\text{Al/Si}^* = 0$  sample synthesised with 0.5 M NaOH/0.5 M KOH is caused by the very rapid relaxation of this sample.  $\text{Al/Si}^* = \text{bulk Al/Si}$ .

$^{29}\text{Si}$  resonances assigned to  $\text{Q}^1$ ,  $\text{Q}^2_{\text{b}}$  and  $\text{Q}^2_{\text{p}}$  sites are also identified in the spectra of the C-(N,K-)A-S-H ( $\text{Al/Si}^* = 0.1$ ) samples (Figure 8B). These spectra also contain an additional resonance assigned to Si in paired sites bonded to structurally-incorporated Al in bridging sites (i.e.  $\text{Q}^2(1\text{Al})$ ) in C-A-S-H, located at  $\delta_{\text{iso}} = -82$  ppm in the spectrum for the alkali-free sample.  $\text{Q}^2(1\text{Al})$  sites identified in laboratory-synthesised C-A-S-H samples equilibrated at  $23^\circ\text{C}$  are located at similar  $\delta_{\text{iso}}$  values.<sup>68</sup>

Peaks assigned to  $\text{Q}^1$ ,  $\text{Q}^2_{\text{b}}$ ,  $\text{Q}^2_{\text{p}}$  and  $\text{Q}^2(1\text{Al})$  are shifted by +0.4 to +1 ppm in the spectrum for the Al-containing sample synthesised with 0.5 M NaOH relative to the alkali-free C-A-S-H

sample (Figure 8B), which is consistent with  $^{29}\text{Si}$  MAS NMR spectra of laboratory-synthesised C-(N,K-)A-S-H produced at 20-25°C.<sup>8, 9</sup> The intensity of the  $\text{Q}^1$  peak is also much greater in the presence of Na and/or K in this sample, similar to the spectra for Al-free C-(N,K-)S-H (Figure 8A). Additional  $\text{Q}^3(1\text{Al})$  and  $\text{Q}^3$  resonances at -88.6 and -96.8 ppm are observed in the spectrum of the 0.5 M NaOH sample, indicating the formation of a cross-linked C-(N,K-)A-S-H product. The  $\delta_{\text{iso}}$  value of the  $\text{Q}^3$  site is equivalent to the chemical shift of this site in laboratory-synthesised C-A-S-H equilibrated at 80°C<sup>14</sup> and in Al-tobermorite formed in 2000-year old Roman seawater concrete,<sup>31</sup> and is similar to the chemical shift of this site in (Al-)tobermorites synthesised at 150°C<sup>69</sup> and 175°C.<sup>70, 71</sup> However, the  $\delta_{\text{iso}}$  value of the  $\text{Q}^3(1\text{Al})$  site is shifted by approximately +3 ppm relative to the chemical shift of this site in the aforementioned literature; this is again attributed to the association of a greater proportion of less positively-charged dissolved species (*e.g.*  $\text{Na}^+$  rather than  $\text{Ca}^{2+}$ ) with Si atoms in  $\text{Q}^3(1\text{Al})$  sites, resulting from the much higher alkali concentrations used here.

Each component peak is shifted to a slightly more positive  $\delta_{\text{iso}}$  value by further increasing the alkali hydroxide concentrations of the synthesis solutions to 1 M (Figure 8B, sample 0.5 M NaOH/0.5 M KOH), suggesting additional uptake of  $\text{Na}^+/\text{K}^+/\text{H}^+$  in C-(N,K-)A-S-H interlayers, while the  $\text{Q}^3$  site is no longer identified. The disappearance of the  $\text{Q}^3$  site at a bulk alkali concentration of 1 M, and the presence of  $\text{Q}^3(1\text{Al})$  resonances at -87 to -89 ppm in the Al and alkali-containing samples, are consistent with the features of  $^{29}\text{Si}$  MAS NMR spectra of  $\text{Na}_2\text{CO}_3$  and  $\text{Na}_2\text{SiO}_3$ -activated slag cement pastes cured under ambient conditions,<sup>5, 72</sup> where  $\text{Q}^3(1\text{Al})$ -containing cross-linked C-(N,K-)A-S-H products are sometimes present in this chemical shift range. The identification of  $\text{Q}^3$ -type sites in the C-(N,K-)A-S-H samples equilibrated at 50°C here, rather than the higher temperatures needed to form these structures in C-A-S-H specimens synthesised with Al but without alkali,<sup>14</sup> shows that the formation of -



Al-O-Si- cross-links in C-(N,K-)A-S-H products is greatly promoted at higher alkali content. The intensity of the  $Q^1$  peaks are further increased by increasing the alkali hydroxide concentration to 1 M.

### 3.6 Structural models and implications

Al/Si ratios, MCLs and cross-linked phase fractions for the C-(N,K-)A-S-H products (Figure 9) are calculated using the  $^{29}\text{Si}$  MAS NMR spectral deconvolution results (Figure 8 and Appendix S8, Electronic Supporting Information) and the ‘Cross-linked Substituted Tobermorite Model’ (CSTM),<sup>37</sup> by representing this phase as a mixture of cross-linked and non-cross-linked tobermorite-like components.

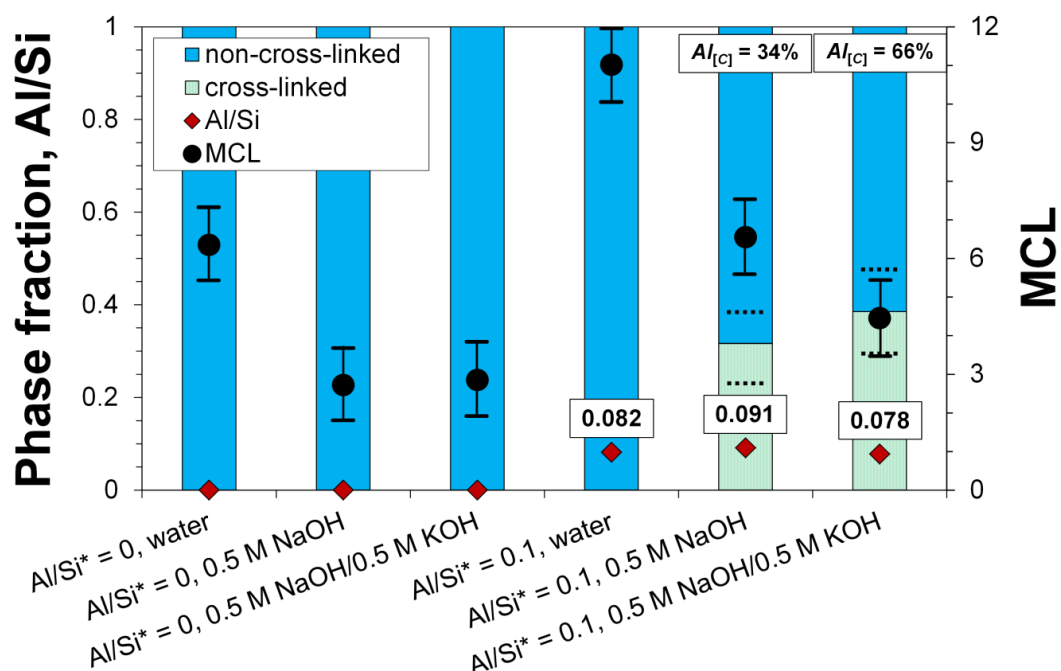


Figure 9. C-(N,K-)S-H and C-(N,K-)A-S-H structural parameters calculated from deconvolution analysis of the  $^{29}\text{Si}$  MAS NMR spectra (Figure 8), determined using the ‘Cross-linked Substituted Tobermorite Model’ (CSTM)<sup>37</sup> for mixed cross-linked/non-cross-linked tobermorite-like phases. The expected error bounds of the deconvolution results are represented by symbol size for the Al/Si ratios, by dotted black lines for the cross-linked phase fractions and by error bars for the MCL values.  $Al_{I[C]}$  = percentage of Al in cross-linked C-(N,K-)A-S-H (eq.(1)). Al/Si\* = bulk Al/Si.

The results obtained by applying the CSTM<sup>37</sup> to the <sup>29</sup>Si MAS NMR spectral deconvolutions show that the MCLs of the C-(N,K-)A-S-H products decrease with increasing alkali concentration, due mainly to the much greater prevalence of Q<sup>1</sup> sites in the presence of Na and/or K (Figure 8). The calculated MCLs are also lower in the systems containing less Al. The calculated Al/Si ratios are similar to the Al/Si\* ratios used in synthesis (Al/Si\* = 0.1), with the small differences explained by the formation of small amounts of C<sub>3</sub>AH<sub>6</sub>/Al(OH)<sub>3</sub> in the alkali-free and 0.5 M NaOH/0.5 M KOH samples, and C<sub>4</sub>Ach<sub>11</sub>/C<sub>3</sub>AH<sub>6</sub>/Al(OH)<sub>3</sub> in the 0.5 M NaOH sample (Appendix S7, Electronic Supporting Information).<sup>14</sup> The alkali and Al-containing C-(N,K-)A-S-H products show similar levels of cross-linking, although the percentage of Al in the cross-linked components ( $Al_{[C]}$ ) of this phase is higher in the sample synthesised using 0.5 M NaOH/0.5 M KOH (66%) relative to the sample synthesised with 0.5 M NaOH (34%).

The calculated  $Al_{[C]}$  values (Figure 9) show that the uptake of Al into cross-linked C-(N,K-)A-S-H components is enhanced as the bulk alkali hydroxide concentration is increased, but also that there is not an extremely strong preference for partitioning of Al into either one of the two structural types. This view is supported by recent work on the role of Al in cross-linking of C-(N,K-)A-S-H in Na<sub>2</sub>SiO<sub>3</sub>-activated slag cements cured for 1-180 days at room temperature, which reported  $Al_{[C]}$  values of 40-60%.<sup>72</sup>

The key alkali-dependent structural changes are therefore: reduced MCL (Figure 9); increased basal spacings at Ca/Si\* ratios < 1 (Figure 6); and increased cross-linking and  $Al_{[C]}$  (in the presence of Al, Figure 9) at higher alkali hydroxide concentrations. A comparison of these structural changes with the slightly reduced C-(N,K-)A-S-H solubilities determined at higher alkali hydroxide concentration and Ca/(Al+Si) ratios ≤ 1 (section 3.4) suggests that the

solubility and MCL of this phase may be directly related in this range of Ca/(Al+Si) ratios. The influence of Ca composition on C-(N,K-)A-S-H solubility dominates at higher Ca/(Al+Si) ratios, *i.e.* at low MCL values, demonstrated by large reductions in the solubility of this phase as a function of increasing Ca/(Al+Si) ratio at the limit  $MCL \rightarrow 2$  (region A in Figure 10). The Ca/(Al+Si) ratios obtained by mass balance and marked in the legend in Figure 10 reflect the total amount of Ca in C-(N,K-)A-S-H; this parameter does not distinguish between Ca present as charge-balancing cations in the interlayer or adsorbed on external surfaces, or structurally-bound in Ca-O sheets (Figure 1), whereas the MCL parameter describes the structure of the (alumino)silicate chains and Ca-O sheets only.

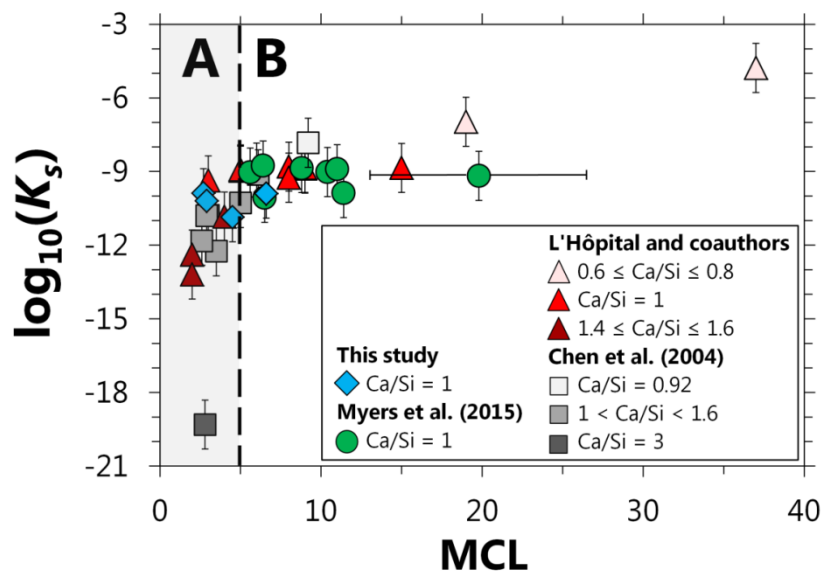


Figure 10. Solubility products for C-(N,K-)A-S-H plotted as a function of MCL, calculated using the dissolution reaction shown in eq.(5) with regions: A) describing C-(N,K-)A-S-H with highly variable Ca/(Al+Si) ratios and slightly variable MCL; and B) describing C-(N,K-)A-S-H with variable Ca/(Al+Si) and MCL. The references for the symbols used are: blue diamonds, this study; green circles, C-(A-)S-H equilibrated at 7-80°C in <sup>14</sup>; red triangles, C-(N,K-)A-S-H equilibrated at 20°C in <sup>8, 60</sup>; and grey squares, C-S-H equilibrated at 22°C in <sup>73</sup>. Solubility products are calculated using H<sub>2</sub>O/Si = 1.2 and Ca/Si ratios taken directly from the literature for the data in <sup>73</sup>, or specified to have a total of 1 mole Si + Al with Ca/Si and Al/Si ratios equivalent to the bulk Ca-Al-Si compositions used, Na/Si ratios = 0.2 for the Na-containing phases, K/Si ratios = 0.2 for the K-containing phases and H<sub>2</sub>O/Si ratios = 1.2 for the data in <sup>8, 14, 60</sup> and in this study. The expected experimental uncertainty is represented by error bars, or by the size of the symbols used in the absence of horizontal error bars for MCL values.

The effects of MCL and  $\text{Ca}/(\text{Al}+\text{Si})$  ratio on C-(N,K-)A-S-H solubility cannot be distinguished from one another in region B of Figure 10 because C-(N,K-)A-S-H can contain many different total  $\text{Ca}/(\text{Al}+\text{Si})$  ratios at a fixed MCL value, for  $\text{MCL} > 5$ .<sup>59</sup> Therefore, selected solubility data for C-(N,K-)A-S-H with  $\text{Ca}/(\text{Al}+\text{Si}) = 1$  were plotted as a function of MCL in Figure 11.

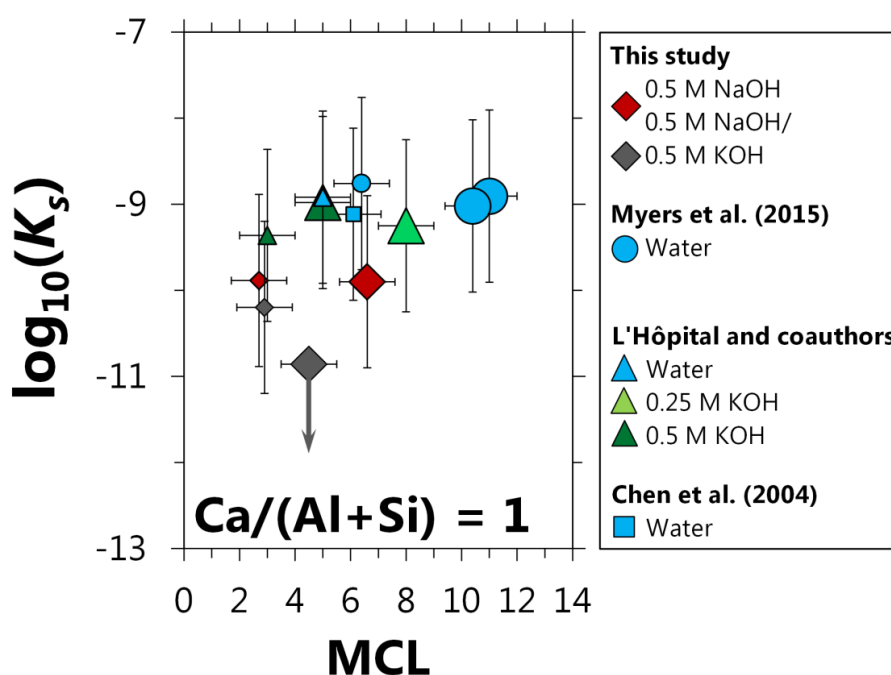


Figure 11. Solubility products for C-(N,K-)A-S-H plotted as a function of the MCL, calculated using the dissolution reaction shown in eq.(5) at a  $\text{Ca}/(\text{Al}+\text{Si})$  ratio = 1. The references for the symbols used are: diamonds, this study ( $\text{Ca}/\text{Si}^* = 1$ ); circles, C-(A-)S-H synthesised with  $\text{Ca}/\text{Si}^* = 1$  and equilibrated at 20-50°C in<sup>14</sup>; triangles, C-(N,K-)A-S-H synthesised with  $\text{Ca}/\text{Si}^* = 1$  and equilibrated at 20°C in<sup>8, 60</sup>; and square, C-S-H equilibrated at 22°C with  $\text{Ca}/\text{Si} = 1.03$  in<sup>73</sup>. Large symbols are data at  $\text{Al}/\text{Si}^* = 0.1$  and small symbols are data at  $\text{Al}/\text{Si}^* = 0$ . C-(N,K-)A-S-H solubility products are calculated using  $\text{H}_2\text{O}/\text{Si} = 1.2$  and  $\text{Ca}/\text{Si}$  ratios taken directly from the literature for the datum in<sup>73</sup>, or specified to have a total of 1 mole Si + Al with  $\text{Ca}/\text{Si}$  and  $\text{Al}/\text{Si}$  ratios equivalent to the bulk Ca-Al-Si compositions used,  $\text{Na}/\text{Si}$  ratios = 0.2 for the Na-containing phases,  $\text{K}/\text{Si}$  ratios = 0.2 for the K-containing phases and  $\text{H}_2\text{O}/\text{Si}$  ratios = 1.2 for the data in<sup>8, 14, 60</sup> and in this study. Error bars represent the expected experimental uncertainty except for the point with a downward-pointing arrow, which additionally represents a maximum solubility product value, as described in the text for Figure 7.

Figure 11 shows an inverse correlation between MCL and the bulk alkali hydroxide concentration, in good agreement with the  $^{29}\text{Si}$  MAS NMR results presented in Figure 9, and also slightly reduced C-(N,K-)A-S-H solubility products in samples synthesised with more highly concentrated alkali hydroxide solutions, consistent with the trends in C-(N,K-)A-S-H solubility shown in Figure 7 at  $\text{Ca}/(\text{Al}+\text{Si}) = 1$ . However, Figure 11 does not show a significant difference in C-(N,K-)A-S-H solubility as a function of Al content, despite the longer chain lengths of the Al-containing C-(N,K-)A-S-H phases compared to their Al-free counterparts. Therefore, these results indicate that the MCL structural parameter does not play a key role in influencing the solubility of C-(N,K-)A-S-H at a  $\text{Ca}/(\text{Al}+\text{Si})$  ratio = 1. This analysis is consistent with recently reported results for C-(A-)S-H that showed comparable solubility products for this phase independent of the Al content.<sup>14</sup>

Alternative factors that could account for the slightly stabilised C-(N,K-)A-S-H structures identified here at increased bulk alkali hydroxide concentrations and  $\text{Ca}/(\text{Al}+\text{Si})$  ratios  $\leq 1$  (Figure 7) would then need to be proposed: increased cross-linking (Figure 9) or changes to the nanoparticulate layered structure of this phase (Figure 6 and <sup>59</sup>) could be potential candidates. However, the large uncertainty ( $\pm 1 \log_{10}$  unit) of the solubility products calculated here (Figure 7) and the limited availability of solubility data for C-(N,K-)A-S-H at  $\text{Ca}/(\text{Al}+\text{Si})$  ratios  $< 1$  mean that these proposed structure-solubility relationships cannot be considered fully conclusive. Further work clarifying the role of structure on the solubility of C-(N,K-)A-S-H would be greatly beneficial in further enabling the design of chemically-stable and durable cementitious binders based on engineering controls such as the mix design and curing temperature.

#### 4. Conclusions

The effect of alkali, Al and Ca on the structure and solubility of C-(N,K-)A-S-H equilibrated at 50°C was investigated in this paper. In general, similar composition-solubility-structure trends are observed at 20°C to those identified here. The long-range order of the alkali-containing C-(N,K-)A-S-H products was much greater than in those synthesised in the absence of alkalis. C-(N,K-)A-S-H basal spacings were generally greater at lower Ca content and at higher alkali concentrations in the samples synthesised using alkaline hydroxide solutions; this latter factor was attributed to the uptake of additional  $\text{Na}^+/\text{K}^+$  species in C-(N,K-)A-S-H interlayers. However, no clear trend in basal spacing as a function of Al content was identified here, in contrast to results reported for this phase at 20°C.

The concentrations of Ca decreased and the concentrations of Si and Al increased in the supernatants as functions of increasing alkali hydroxide concentration. More alkali was incorporated in C-(N,K-)A-S-H synthesised with lower Ca and higher alkali hydroxide concentrations. Alkali uptake in this phase was found to be independent, within the experimental uncertainty, of the alkali type (Na or K) and Al/Si ratio at the relatively low amounts of Al added to each sample (bulk Al/Si  $\leq 0.05$ ).

Shorter mean chain lengths, increased cross-linking, and incorporation of more Al into cross-linked C-(N,K-)A-S-H components were identified upon increasing the bulk alkali and Al content. Mixed cross-linked/non-cross-linked C-(N,K-)A-S-H was only formed in the presence of both alkali and Al. A reduction in C-(N,K-)A-S-H solubility was found at higher bulk alkali hydroxide concentrations, but this result was only significant for some samples prepared with bulk Ca/Si ratios  $\leq 1$ . The stability of this phase did not vary greatly as a

function of the Al/Si ratio. The reduced C-(N,K-)A-S-H solubility calculated at higher alkali content was discussed to be partly related to structural changes in this phase, and it was tentatively proposed that the MCL does not play a key role in these solubility-structure relationships. These results provide new insight into the composition-structure-solubility relationships in C-(N,K-)A-S-H, which will improve how hydrated alkali and Al-containing cements are understood to perform in service.

## **5. Supporting information**

Electronic Supplementary Information (ESI) available: Appendix S1 contains the details of the structural constraints used to deconvolute the  $^{29}\text{Si}$  MAS NMR spectra; the thermodynamic database used is presented in Appendix S2; tabulated phase quantification results from XRD, TGA and Rietveld analysis are provided in Appendix S3; TGA results are shown in Appendix S4; saturation indices calculated from the measured supernatant concentrations are shown in Appendix S5; tabulated supernatant concentrations and the solubility products for C-(N,K-)A-S-H with chemical compositions determined by mass balance are provided in Appendix S6; additional solid and liquid phase data for the  $\text{Al/Si}^* = 0$  and 0.1 C-(N,K-)A-S-H samples studied by  $^{29}\text{Si}$  MAS NMR are presented in Appendix S7; and detailed  $^{29}\text{Si}$  MAS NMR spectral deconvolution results are provided in Appendix S8.

## **6. Acknowledgements**

The authors thank Salaheddine Alahrache and Daniel Rentsch for assistance with NMR spectroscopy, Boris Ingold for assistance with XRD, Ellina Bernard, Boris Ingold and Nikolajs Toropovs for assistance with TGA, and the Swiss National Science Foundation grant

n° 130419 for the financial support of E. L'Hôpital. The NMR hardware was partially granted by the Swiss National Science Foundation (grant 206021\_150638/1).

## 7. References

1. H. F. W. Taylor, *Cement Chemistry*, Thomas Telford Publishing, London, 1997.
2. A. Fernández-Jiménez and A. Palomo, *Fuel*, 2003, **82**, 2259-2265.
3. J. L. Provis and S. A. Bernal, *Annu. Rev. Mater. Res.*, 2014, **44**, 299-327.
4. R. Snellings, *J. Am. Ceram. Soc.*, 2013, **96**, 2467-2475.
5. S. A. Bernal, J. L. Provis, R. J. Myers, R. San Nicolas and J. S. J. van Deventer, *Mater. Struct.*, 2015, **48**, 517-529.
6. T. Chappex and K. Scrivener, *Cem. Concr. Res.*, 2012, **42**, 1049-1054.
7. A. Leemann, G. Le Saout, F. Winnefeld, D. Rentsch and B. Lothenbach, *J. Am. Ceram. Soc.*, 2011, **94**, 1243-1249.
8. E. L'Hôpital, B. Lothenbach, G. Le Saoût, D. A. Kulik and K. Scrivener, *Cem. Concr. Res.*, submitted.
9. I. Lognot, I. Klur and A. Nonat, in *Nuclear magnetic resonance spectroscopy of cement-based materials*, eds. P. Colombet, H. Zanni, A.-R. Grimmer and P. Sozzani, Springer, Berlin, 1998, ch. 13, pp. 189-196.
10. J. Duchesne and E. J. Reardon, *Cem. Concr. Res.*, 1995, **25**, 1043-1053.
11. T. T. H. Bach, E. Chabas, I. Pochard, C. Cau-dit-Coumes, J. Haas, F. Frizon and A. Nonat, *Cem. Concr. Res.*, 2013, **51**, 14-21.
12. I. G. Richardson and G. W. Groves, *J. Mater. Sci.*, 1993, **28**, 265-277.
13. I. G. Richardson, *Cem. Concr. Res.*, 2008, **38**, 137-158.



- 759 14. R. J. Myers, E. L'Hôpital, J. L. Provis and B. Lothenbach, *Cem. Concr. Res.*, 2015, **68**,  
760 83-93.
- 761 15. L. Pegado, C. Labbez and S. V. Churakov, *J. Mater. Chem. A*, 2014, **2**, 3477-3483.
- 762 16. M. D. Andersen, H. J. Jakobsen and J. Skibsted, *Cem. Concr. Res.*, 2006, **36**, 3-17.
- 763 17. G. Renaudin, J. Russias, F. Leroux, C. Cau dit Coumes and F. Frizon, *J. Solid State*  
764 *Chem.*, 2009, **182**, 3320-3329.
- 765 18. G. K. Sun, J. F. Young and R. J. Kirkpatrick, *Cem. Concr. Res.*, 2006, **36**, 18-29.
- 766 19. C. Labbez, I. Pochard, B. Jönsson and A. Nonat, *Cem. Concr. Res.*, 2011, **41**, 161-168.
- 767 20. E. Bonaccorsi, S. Merlino and A. R. Kampf, *J. Am. Ceram. Soc.*, 2005, **88**, 505-512.
- 768 21. S. Y. Hong and F. P. Glasser, *Cem. Concr. Res.*, 1999, **29**, 1893-1903.
- 769 22. D. E. Macphee, K. Luke, F. P. Glasser and E. E. Lachowski, *J. Am. Ceram. Soc.*,  
770 1989, **72**, 646-654.
- 771 23. G. L. Kalousek, *J. Res. Natl. Bur. Stand.*, 1944, **32**, 285-302.
- 772 24. S. J. Way and A. Shayan, *Cem. Concr. Res.*, 1992, **22**, 915-926.
- 773 25. H. Stade, *Cem. Concr. Res.*, 1989, **19**, 802-810.
- 774 26. P. Nieto and H. Zanni, *J. Mater. Sci.*, 1997, **32**, 3419-3425.
- 775 27. B. Lothenbach, G. Le Saout, M. Ben Haha, R. Figi and E. Wieland, *Cem. Concr. Res.*,  
776 2012, **42**, 410-423.
- 777 28. R. J. Myers, S. A. Bernal and J. L. Provis, *Cem. Concr. Res.*, 2014, **66**, 27-47.
- 778 29. B. Lothenbach, K. Scrivener and R. D. Hooton, *Cem. Concr. Res.*, 2011, **41**, 1244-  
779 1256.
- 780 30. R. Taylor, I. G. Richardson and R. M. D. Brydson, *Cem. Concr. Res.*, 2010, **40**, 971-  
781 983.

- 782 31. M. D. Jackson, S. R. Chae, S. R. Mulcahy, C. Meral, R. Taylor, P. Li, A.-H. Emwas, J.  
783 Moon, S. Yoon, G. Vola, H.-R. Wenk and P. J. M. Monteiro, *Am. Mineral.*, 2013, **98**,  
784 1669-1687.
- 785 32. H. Viallis, P. Faucon, J. C. Petit and A. Nonat, *J. Phys. Chem. B*, 1999, **103**, 5212-  
786 5219.
- 787 33. J. Skibsted and M. D. Andersen, *J. Am. Ceram. Soc.*, 2013, **96**, 651-656.
- 788 34. S. Y. Hong and F. P. Glasser, *Cem. Concr. Res.*, 2002, **32**, 1101-1111.
- 789 35. E. L'Hôpital, B. Lothenbach, K. Scrivener and D. A. Kulik, *Cem. Concr. Res.*,  
790 submitted.
- 791 36. B. H. O'Connor and M. D. Raven, *Powder Diffr.*, 1988, **3**, 2-6.
- 792 37. R. J. Myers, S. A. Bernal, R. San Nicolas and J. L. Provis, *Langmuir*, 2013, **29**, 5294-  
793 5306.
- 794 38. D. A. Kulik, T. Wagner, S. V. Dmytrieva, G. Kosakowski, F. F. Hingerl, K. V.  
795 Chudnenko and U. Berner, *Comput. Geosci.*, 2013, **17**, 1-24.
- 796 39. T. Wagner, D. A. Kulik, F. F. Hingerl and S. V. Dmytrieva, *Can. Mineral.*, 2012, **50**,  
797 1173-1195.
- 798 40. T. Thoenen, W. Hummel and U. Berner, *Mineral. Mag.*, 2013, **77**, 2327.
- 799 41. W. Hummel, U. Berner, E. Curti, F. J. Pearson and T. Thoenen, *Nagra/PSI Chemical*  
800 *Thermodynamic Database 01/01*, Universal Publishers, Parkland, Florida, 2002.
- 801 42. D. A. Kulik and M. Kersten, *J. Am. Ceram. Soc.*, 2001, **84**, 3017-3026.
- 802 43. B. Lothenbach, T. Matschei, G. Möschner and F. P. Glasser, *Cem. Concr. Res.*, 2008,  
803 **38**, 1-18.
- 804 44. B. Lothenbach and F. Winnefeld, *Cem. Concr. Res.*, 2006, **36**, 209-226.
- 805 45. T. Matschei, B. Lothenbach and F. P. Glasser, *Cem. Concr. Res.*, 2007, **37**, 1379-1410.

- 806 46. G. Möschner, B. Lothenbach, J. Rose, A. Ulrich, R. Figi and R. Kretzschmar,  
807 *Geochim. Cosmochim. Acta*, 2008, **72**, 1-18.
- 808 47. G. Möschner, B. Lothenbach, F. Winnefeld, A. Ulrich, R. Figi and R. Kretzschmar,  
809 *Cem. Concr. Res.*, 2009, **39**, 482-489.
- 810 48. T. Schmidt, B. Lothenbach, M. Romer, K. Scrivener, D. Rentsch and R. Figi, *Cem.*  
811 *Conc. Res.*, 2008, **38**, 337-349.
- 812 49. D. A. Kulik and M. Kersten, *Environ. Sci. Technol.*, 2002, **36**, 2926-2931.
- 813 50. B. Lothenbach, L. Pelletier-Chaignat and F. Winnefeld, *Cem. Concr. Res.*, 2012, **42**,  
814 1621-1634.
- 815 51. B. Z. Dilnesa, B. Lothenbach, G. Renaudin, A. Wichser and D. Kulik, *Cem. Concr.*  
816 *Res.*, 2014, **59**, 96-111.
- 817 52. H. C. Helgeson, D. H. Kirkham and G. C. Flowers, *Am. J. Sci.*, 1981, **281**, 1249-1516.
- 818 53. Y. Lee, Y. Lee and D. Seoung, *Am. Mineral.*, 2010, **95**, 1636-1641.
- 819 54. T. Runčevski, R. E. Dinnebier, O. V. Magdysyuk and H. Pöllmann, *Acta Crystallogr.*  
820 *B*, 2012, **68**, 493-500.
- 821 55. P. Faucon, J. C. Petit, T. Charpentier, J. F. Jacquinet and F. Adenot, *J. Am. Ceram.*  
822 *Soc.*, 1999, **82**, 1307-1312.
- 823 56. X. Pardal, I. Pochard and A. Nonat, *Cem. Concr. Res.*, 2009, **39**, 637-643.
- 824 57. H. M. Jennings, *Cem. Concr. Res.*, 2008, **38**, 275-289.
- 825 58. A. C. A. Muller, K. L. Scrivener, A. M. Gajewicz and P. J. McDonald, *Micropor.*  
826 *Mesopor. Mat.*, 2013, **178**, 99-103.
- 827 59. I. Richardson, *Acta Crystallogr. B*, 2014, **70**, 903-923.
- 828 60. E. L'Hôpital, Ph.D. Thesis, École Polytechnique Fédérale de Lausanne, 2014.
- 829 61. S. Grangeon, F. Claret, Y. Linard and C. Chiaberge, *Acta Crystallogr. B*, 2013, **69**,  
830 465-473.

62. G. Renaudin, J. Russias, F. Leroux, F. Frizon and C. Cau dit Coumes, *J. Solid State Chem.*, 2009, **182**, 3312-3319.
63. K. Garbev, G. Beuchle, M. Bornefeld, L. Black and P. Stemmermann, *J. Am. Ceram. Soc.*, 2008, **91**, 3005-3014.
64. B. E. Conway, *Ionic hydration in chemistry and biophysics*, Elsevier Scientific, Amsterdam, 1981.
65. X. Cong and R. J. Kirkpatrick, *Adv. Cem. Based Mater.*, 1996, **3**, 144-156.
66. F. Brunet, P. Bertani, T. Charpentier, A. Nonat and J. Virlet, *J. Phys. Chem. B*, 2004, **108**, 15494-15502.
67. P. Rejmak, J. S. Dolado, M. J. Stott and A. Ayuela, *J. Phys. Chem. C*, 2012, **116**, 9755-9761.
68. X. Pardal, F. Brunet, T. Charpentier, I. Pochard and A. Nonat, *Inorg. Chem.*, 2012, **51**, 1827-1836.
69. J. Houston, R. Maxwell and S. Carroll, *Geochem. Trans.*, 2009, **10**, 1-14.
70. M. Tsuji, S. Komarneni and P. Malla, *J. Am. Ceram. Soc.*, 1991, **74**, 274-279.
71. X. Cong and R. J. Kirkpatrick, *Adv. Cem. Based Mater.*, 1996, **3**, 133-143.
72. R. J. Myers, S. A. Bernal, J. L. Provis, J. D. Gehman and J. S. J. van Deventer, *J. Am. Ceram. Soc.*, 2015, **98**, 996-1004.
73. J. J. Chen, J. J. Thomas, H. F. W. Taylor and H. M. Jennings, *Cem. Concr. Res.*, 2004, **34**, 1499-1519.